

Commercial Lumber, Round Timbers, and Ties

David E. Kretschmann, Research General Engineer

Contents

| |
|---|
| Hardwood Lumber 6–2 |
| Factory Lumber 6–2 |
| Dimension and Component Parts 6–4 |
| Finished Market Products 6–4 |
| Lumber Species 6–6 |
| Softwood Lumber 6–6 |
| Lumber Grades 6–7 |
| Lumber Manufacture 6–10 |
| Softwood Lumber Species 6–11 |
| Softwood Lumber Grading 6–12 |
| Purchase of Lumber 6–12 |
| Retail Yard Inventory 6–12 |
| Important Purchase Considerations 6–17 |
| Round Timbers and Ties 6–18 |
| Standards and Specifications 6–18 |
| Material Requirements 6–18 |
| Availability 6–19 |
| Form 6–20 |
| Weight and Volume 6–21 |
| Durability 6–22 |
| Preservative Treatment 6–22 |
| Service Life 6–22 |
| Commonly Used Lumber, Round Timber, and Tie Abbreviations 6–23 |
| References 6–25 |

When sawn, a log yields round timber, ties, or lumber of varying quality. This chapter presents a general discussion of grading, standards, and specifications for these commercial products.

In a broad sense, commercial lumber is any lumber that is bought or sold in the normal channels of commerce. Commercial lumber may be found in a variety of forms, species, and types, and in various commercial establishments, both wholesale and retail. Most commercial lumber is graded by standardized rules that make purchasing more or less uniform throughout the country.

Round timbers and ties represent some of the most efficient uses of our forest resources. They require a minimum of processing between harvesting the tree and marketing the structural commodity. Poles and piles are debarked or peeled, seasoned, and often treated with preservative prior to use as structural members. Construction logs are usually shaped to facilitate construction. Ties, used for railroads, landscaping, and mining, are slab-cut to provide flat surfaces. Because these products are relatively economical to produce compared with glulam, steel, and concrete products, they are commonly used throughout the United States.

To enable users to buy the quality that best suits their purposes, lumber, round timbers, and ties are graded into use categories, each having an appropriate range in quality.

Generally, the grade of a piece of wood is based on the number, character, and location of features that may lower its strength, durability, or utility value. Among the more common visual features are knots, checks, pitch pockets, shake, and stain, some of which are a natural part of the tree. Some grades are free or practically free from these features. Other grades, which constitute the great bulk of solid wood products, contain fairly numerous knots and other features. With proper grading, lumber containing these features is entirely satisfactory for many uses.

The grading operation for most solid wood products takes place at the sawmill. Establishment of grading procedures is largely the responsibility of manufacturers' associations. Because of the wide variety of wood species, industrial practices, and customer needs, different grading practices coexist. The grading practices of most interest are considered in the sections that follow, under the major categories of hardwood lumber and softwood lumber, round timbers, and ties.

Hardwood Lumber

The principal use of hardwood lumber is for remanufacture into furniture, cabinetwork, and pallets or direct use as flooring, paneling, moulding, and millwork. Hardwood lumber is graded and marketed in three main categories: Factory lumber, dimension parts, and finished market products. Several hardwood species are graded under the American Softwood Lumber Standard and sold as structural lumber (Chap. 7). Also, specially graded hardwood lumber can be used for structural glued-laminated lumber.

Prior to 1898, hardwoods were graded by individual mills for local markets. In 1898, manufacturers and users formed the National Hardwood Lumber Association to standardize grading for hardwood lumber. Between 1898 and 1932, grading was based on the number and size of visual features. In 1932, the basis for grading was changed to standard clear-cutting sizes.

Both Factory lumber and dimension parts are intended to serve the industrial customer. The important difference is that for Factory lumber, the grades reflect the proportion of a piece that can be cut into useful smaller pieces, whereas the grades for dimension parts are based on use of the entire piece. Finished market products are graded for their unique end-use with little or no remanufacture. Examples of finished products include moulding, stair treads, and hardwood flooring.

Factory Lumber


Grades

The rules adopted by the National Hardwood Lumber Association are considered standard in grading hardwood lumber

intended for cutting into smaller pieces to make furniture or other fabricated products. In these rules, the grade of a piece of hardwood lumber is determined by the proportion of a piece that can be cut into a certain number of smaller pieces of material, commonly called cuttings, which are generally clear on one side, have the reverse face sound, and are not smaller than a specified size.

The best grade in the Factory lumber category is termed FAS (Firsts and Seconds). The second grade is F1F (FAS one face). The third grade is Selects, which is followed by No. 1 Common, No. 2A Common, No. 2B Common, No. 3A Common, No. 3B Common, and Sound Wormy. Except for F1F and Selects, the poorer side of a piece is inspected for grade assignment. Standard hardwood lumber grades are described in Table 6-1. This table illustrates, for example, that FAS includes pieces that will allow at least 83-1/3% of their surface measure to be cut into clear face material. Except for Sound Wormy, the minimum acceptable length, width, surface measure, and percentage of piece that must work into a cutting decrease with decreasing grade. Figure 6-1 is an example of grading for cuttings.

This brief summary of grades for Factory lumber should not be regarded as a complete set of grading rules, because many details, exceptions, and special rules for certain species are not included. The complete official rules of the National Hardwood Lumber Association (NHLA) should be followed as the only full description of existing grades (see Table 6-2 for addresses of NHLA and other U.S. hardwood grading associations). Table 6-3 lists names of commercial domestic hardwood species that are graded by NHLA rules.

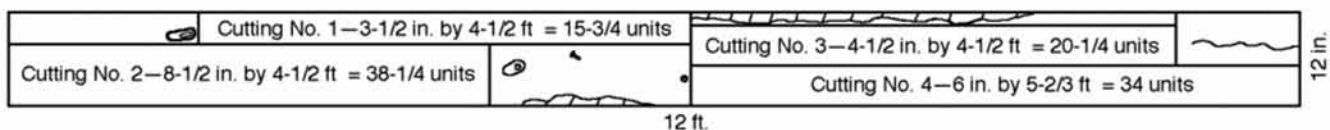

1. Determine Surface Measure (S.M.) using lumber scale stick or from formula:

$$\frac{\text{Width in inches} \times \text{length in feet}}{12} = \frac{12 \text{ in.} \times 12 \text{ ft}}{12}$$

= 12 ft² S.M.

2. No. 1 Common is assumed grade of board. Percent of clear-cutting area required for No. 1 Common—66²/₃% or ⁸/₁₂.

3. Determine maximum number of cuttings permitted.

$$\text{For No. 1 Common grade (S.M. + 1) } \div 3$$

$$= \frac{(12 + 1)}{3} = \frac{13}{3} = 4 \text{ cuttings.}$$

4. Determine minimum size of cuttings.

For No. 1 Common grade 4 in. x 2 ft or 3 in. x 3 ft.

5. Determine clear-face cutting units needed.

$$\text{For No. 1 Common grade S.M.} \times 8 = 12 \times 8$$

$$= 96 \text{ units}$$

6. Determine total area of permitted clear-face cutting in units.

Width in inches and fractions of inches
x length in feet and fractions of feet

$$\text{Cutting \#1—} 3\frac{1}{2} \text{ in.} \times 4\frac{1}{2} \text{ ft} = 15\frac{3}{4} \text{ units}$$

$$\text{Cutting \#2—} 8\frac{1}{2} \text{ in.} \times 4\frac{1}{2} \text{ ft} = 38 \text{ units}$$

$$\text{Cutting \#3—} 4\frac{1}{2} \text{ in.} \times 4\frac{1}{2} \text{ ft} = 20\frac{1}{4} \text{ units}$$

$$\text{Cutting \#4—} 6 \text{ in.} \times 5\frac{2}{3} \text{ ft} = 34 \text{ units}$$

$$\text{Total Units} \quad 108$$

Units required for No. 1 Common—96.

7. Conclusion: Board meets requirements for No. 1 Common grade.

Figure 6-1. Example of hardwood grading for cuttings using No. 1 Common lumber grade. Current grading rules are written only in the inch-pound system of measurement. Standard lengths are in 1-ft increments.

Table 6–1. Standard hardwood lumber grades^{a,b}

| Grade and allowable lengths | Allowable width (in.) | Allowable surface measure of pieces (ft ²) | Minimum amount of piece in clearface cuttings (%) | Allowable cuttings | |
|---|-----------------------|--|---|--------------------|---------------------------------|
| | | | | Maximum no. | Minimum size |
| FAS | 6+ | 4 to 7 | 83-1/3 | 1 | 4 in. by 5 ft |
| 8 to 16 ft | | 6 and 7 | 91-2/3 | 2 | or |
| and | | 8 to 11 | 83-1/3 | 2 | 3 in. by 7 ft |
| F1F | | 8 to 11 | 91-2/3 | 3 | |
| 8 to 16 ft ^c | | 12 to 15 | 83-1/2 | 3 | |
| | | 12 to 15 | 91-2/3 | 4 | |
| | | 16+ | 83-1/3 | 4 | |
| Selects 6 to 16 ft | 4+ | 2 and 3 | 91-2/3 | 1 | 4 in. by 5 ft |
| | | 4+ | — ^d | | or |
| | | | | | 3 in. by 7 ft |
| No. 1 Common 4 to 16 ft (only 5% of minimum width is allowed) | 3+ | 1 | 100 | 0 | 4 in. by 2 ft |
| | | 2 | 75 | 1 | or |
| | | 3 and 4 | 66-2/3 | 1 | 3 in. by 3 ft |
| | | 3 and 4 | 75 | 2 | |
| | | 5 to 7 | 66-2/3 | 2 | |
| | | 5 to 7 | 75 | 3 | |
| | | 8 to 10 | 66-2/3 | 3 | |
| | | 11 to 13 | 66-2/3 | 4 | |
| | | 14+ | 66-2/3 | 5 | |
| No. 2 Common 4 to 16 ft | 3+ | 1 | 66-2/3 | 1 | 3 in. by 2 ft |
| | | 2 and 3 | 50 | 1 | |
| | | 2 and 3 | 66-2/3 | 2 | |
| | | 4 and 5 | 50 | 2 | |
| | | 4 and 5 | 66-2/3 | 3 | |
| | | 6 and 7 | 50 | 3 | |
| | | 6 and 7 | 66-2/3 | 4 | |
| | | 8 and 9 | 50 | 4 | |
| | | 10 and 11 | 50 | 5 | |
| | | 12 and 13 | 50 | 6 | |
| | | 14+ | 50 | 7 | |
| No. 3A Common 4 to 16 ft | 3+ | 1+ | 33-1/3 ^f | — ^g | 3 in. by 2 ft |
| No. 3B Common 4 to 16 ft | 3+ | 1+ | 25 ^h | — ^g | 1-1/2 in. by 36 in ² |
| Sound Wormy ^e | | | | | |

^aCurrent grading rules are written only in the inch–pound system of measurement.

^bInspection made on poorer side of piece, except in Selects grade.

^cFAS is a grade that designates Firsts and Seconds. F1F is a grade that designates FAS one face.

^dSame as F1F, with reverse side of board not below No. 1 Common.

^eSound Wormy grade shall not be below No. 1 Common except that the natural characteristics of worm holes, bird pecks, stain, sound knot not exceeding 3/4 in. in diameter are admitted. Other sound defects that do not exceed in extent or damage the defects described are admitted in the cuttings. Unless otherwise specified, Sound Wormy shall include the full product of the log in No. 1 Common and Better Sound Wormy.

^fAlso admits pieces that grade not below No. 2 Common on the good face and reverse side of sound cuttings.

^gUnlimited.

^hCuttings must be sound; clear face not required.

Standard Dimensions

Standard lengths of hardwood lumber are in 305-mm (1-ft) increments from 1.2 to 4.9 m (4 to 16 ft). Standard thickness values for hardwood lumber, rough and surfaced on two sides (S2S), are given in Table 6–4. The thickness of S1S lumber is subject to contract agreement. Abbreviations commonly used in contracts and other documents for the purchase and sale of lumber are listed at the end of this chapter.

Hardwood lumber is usually manufactured to random width. The hardwood lumber grades do not specify standard

widths; however, the grades do specify minimum width for each grade as follows:

| Grade | Minimum width (mm (in.)) |
|------------------------------|--------------------------|
| FAS | 152 (6) |
| F1F | 152 (6) |
| Selects | 102 (4) |
| No. 1, 2A, 2B, 3A, 3B Common | 76 (3) |

Table 6–2. Hardwood grading associations in United States^a

| Name and address | Species covered by grading rules (products) |
|--|---|
| National Hardwood Lumber Association P.O. Box 34518 Memphis, TN 38184–0518 www.nhla.com | All hardwood species (furniture cuttings, construction lumber) |
| Wood Components Manufacturers Association 741 Butlers Gate, Suite 100 Marietta, GA 30068 www.woodcomponents.org | All hardwood species (hardwood furniture dimension, squares, laminated stock, interior trim, stair treads and risers) |
| Maple Flooring Manufacturers Association 111 Deer lake Road Suite 100 Deerfield, IL 60015 www.maplefloor.org | Maple, beech, birch (flooring) |
| National Oak Flooring Manufacturers Association 22 N. Front St., Suite 1080 Memphis, TN 38103 www.nofma.org | Oak, ash, pecan, hickory, pecan, beech, birch, hard maple (flooring, including prefinished) |

^aGrading associations that include hardwood species in structural grades are listed in Table 6–5.

If the width is specified by purchase agreement, S1E or S2E lumber is 10 mm (3/8 in.) scant of nominal size in lumber less than 203 mm (8 in.) wide and 13 mm (1/2 in.) scant in lumber ≥203 mm (≥8 in.) wide.

Dimension and Component Parts

The term “dimension parts” for hardwoods signifies stock that is processed in specific thickness, width, and length, or multiples thereof and ranges from semi-machined to completely machined component products. This stock is sometimes referred to as “hardwood dimension stock” or “hardwood lumber for dimension parts.” This stock should not be confused with “dimension lumber,” a term used in the structural lumber market to mean lumber standard 38 mm to less than 89 mm thick (nominal 2 in. to less than 4 in. thick).

Dimension component parts are normally kiln dried and generally graded under the rules of the Wood Components Manufacturers Association (WCMA). These rules encompass three classes of material, each of which is classified into various grades:

| Hardwood dimension parts (flat stock) | Solid kiln-dried squares (rough) | Solid kiln-dried squares (surfaced) |
|---------------------------------------|----------------------------------|-------------------------------------|
| Clear two faces | Clear | Clear |
| Clear one face | Select | Select |
| Paint | Sound | Paint |
| Core | | Second |
| Sound | | |

Each class may be further defined as semifabricated (rough or surfaced) or completely fabricated, including edge-glued panels. The rough wood component parts are blank-sawn and ripped to size. Surfaced semifabricated parts have been

through one or more manufacturing stages. Completely fabricated parts have been completely processed for their end use.

Finished Market Products

Some hardwood lumber products are graded in relatively finished form, with little or no further processing anticipated. Flooring is probably the finished market product with the highest volume. Other examples are lath, siding, ties, planks, carstock, construction boards, timbers, trim, moulding, stair treads, and risers. Grading rules promulgated for flooring anticipate final consumer use and are summarized in this section. Details on grades of other finished products are found in appropriate association grading rules.

Hardwood flooring generally is graded under the rules of the Maple Flooring Manufacturers Association (MFMA) or the National Oak Flooring Manufacturers Association (NOFMA). Tongued-and-grooved, end-matched hardwood flooring is commonly furnished. Square-edge, square-end-strip flooring is also available as well as parquet flooring suitable for laying with mastic.

The grading rules of the Maple Flooring Manufacturers Association cover flooring that is manufactured from hard maple, beech, and birch. Each species is graded into four categories:

- First grade—one face practically free of all imperfections; variations in natural color of wood allowed
- Second grade—tight, sound knots (except on edges or ends) and other slight imperfections allowed; must be possible to lay flooring without waste
- Third grade—may contain all visual features common to hard maple, beech, and birch; will not admit voids on edges or ends, or holes over 10-mm (3/8-in.) in

Chapter 6 Commercial Lumber, Round Timbers, and Ties

Table 6–3. Nomenclature of commercial hardwood lumber

| Commercial name for lumber | Common tree name | Botanical name | Commercial name for lumber | Common tree name | Botanical name |
|----------------------------|---------------------|--------------------------------|----------------------------|------------------------|---|
| Alder, red | Red alder | <i>Alnus rubra</i> | Maple, Oregon | Big leaf maple | <i>Acer macrophyllum</i> |
| Ash, black | Black ash | <i>Fraxinus nigra</i> | Maple, soft | Red maple | <i>Acer rubrum</i> |
| Ash, Oregon | Oregon ash | <i>Fraxinus latifolia</i> | | Silver maple | <i>Acer saccharinum</i> |
| Ash, white | Blue ash | <i>Fraxinus quadrangulata</i> | Oak, red | Black oak | <i>Quercus velutina</i> |
| | Green ash | <i>Fraxinus pennsylvanica</i> | | Blackjack oak | <i>Quercus marilandica</i> |
| | White ash | <i>Fraxinus americana</i> | | California black oak | <i>Quercus kelloggi</i> |
| Aspen (popple) | Bigtooth aspen | <i>Populus grandidentata</i> | | Cherrybark oak | <i>Quercus falcata</i> var. <i>pagodaefolia</i> |
| | Quaking aspen | <i>Populus tremuloides</i> | | Laurel oak | <i>Quercus laurifolia</i> |
| Basswood | American basswood | <i>Tilia americana</i> | | Northern pin oak | <i>Quercus ellipsoidalis</i> |
| | White basswood | <i>Tilia heterophylla</i> | | Northern red oak | <i>Quercus rubra</i> |
| Beech | American beech | <i>Fagus grandifolia</i> | | Nuttall oak | <i>Quercus nuttallii</i> |
| Birch | Gray birch | <i>Betula populifolia</i> | | Pin oak | <i>Quercus palustris</i> |
| | Paper birch | <i>Betula papyrifera</i> | | Scarlet oak | <i>Quercus coccinea</i> |
| | River birch | <i>Betula nigra</i> | | Shumard oak | <i>Quercus shumardii</i> |
| | Sweet birch | <i>Betula lenta</i> | | Southern red oak | <i>Quercus falcata</i> |
| | Yellow birch | <i>Betula alleghaniensis</i> | | Turkey oak | <i>Quercus laevis</i> |
| Boxelder | Boxelder | <i>Acer negundo</i> | | Willow oak | <i>Quercus phellos</i> |
| Buckeye | Ohio buckeye | <i>Aesculus glabra</i> | Oak, white | Arizona white oak | <i>Quercus arizonica</i> |
| | Yellow buckeye | <i>Aesculus octandra</i> | | Blue oak | <i>Quercus douglasii</i> |
| Butternut | Butternut | <i>Juglans cinerea</i> | | Bur oak | <i>Quercus macrocarpa</i> |
| Cherry | Black cherry | <i>Prunus serotina</i> | | Valley oak | <i>Quercus lobata</i> |
| Chestnut | American chestnut | <i>Castanea dentate</i> | | Chestnut oak | <i>Quercus prinus</i> |
| Cottonwood | Balsam poplar | <i>Populus balsamifera</i> | | Chinkapin oak | <i>Quercus muehlenbergii</i> |
| | Eastern cottonwood | <i>Populus deltoids</i> | | Emory oak | <i>Quercus emoryi</i> |
| | Black cottonwood | <i>Populus trichocarpa</i> | | Gambel oak | <i>Quercus gambelii</i> |
| Cucumber | Cucumbertree | <i>Magnolia acuminata</i> | | Mexican blue oak | <i>Quercus oblongifolia</i> |
| Dogwood | Flowering dogwood | <i>Cornus florida</i> | | Live oak | <i>Quercus virginiana</i> |
| | Pacific dogwood | <i>Cornus nuttallii</i> | | Oregon white oak | <i>Quercus garryana</i> |
| Elm, rock | Cedar elm | <i>Ulmus crassifolia</i> | | Overcup oak | <i>Quercus lyrata</i> |
| | Rock elm | <i>Ulmus thomasii</i> | | Post oak | <i>Quercus stellata</i> |
| | September elm | <i>Ulmus serotina</i> | | Swamp chestnut oak | <i>Quercus michauxii</i> |
| | Winged elm | <i>Ulmus alata</i> | | Swamp white oak | <i>Quercus bicolor</i> |
| Elm, soft | American elm | <i>Ulmus Americana</i> | | White oak | <i>Quercus alba</i> |
| | Slippery elm | <i>Ulmus rubra</i> | Oregon myrtle | California-laurel | <i>Umbellularia californica</i> |
| Gum | Sweetgum | <i>Liquidambar styraciflua</i> | Osage orange | Osage-orange | <i>Maclura pomifera</i> |
| Hackberry | Hackberry | <i>Celtis occidentalis</i> | Pecan | Bitternut hickory | <i>Carya cordiformis</i> |
| | Sugarberry | <i>Celtis laevigata</i> | | Nutmeg hickory | <i>Carya myristiciformis</i> |
| Hickory | Mockernut hickory | <i>Carya tomentosa</i> | | Water hickory | <i>Carya aquatica</i> |
| | Pignut hickory | <i>Carya glabra</i> | | Pecan | <i>Carya illinoensis</i> |
| | Shagbark hickory | <i>Carya ovata</i> | Persimmon | Common persimmon | <i>Diospyros virginiana</i> |
| | Shellbark hickory | <i>Carya lacinoso</i> | Poplar | Yellow-poplar | <i>Liriodendron tulipifera</i> |
| Holly | American holly | <i>Ilex opaca</i> | Sassafras | Sassafras | <i>Sassafras albidum</i> |
| Ironwood | Eastern hophornbeam | <i>Ostrya virginiana</i> | Sycamore | Sycamore | <i>Platanus occidentalis</i> |
| Locust | Black locust | <i>Robinia pseudoacacia</i> | Tanoak | Tanoak | <i>Lithocarpus densiflorus</i> |
| | Honeylocust | <i>Gleditsia triacanthos</i> | Tupelo | Black tupelo, blackgum | <i>Nyssa sylvatica</i> |
| Madrone | Pacific madrone | <i>Arbutus menziesii</i> | | Ogeechee tupelo | <i>Nyssa ogeche</i> |
| Magnolia | Southern magnolia | <i>Magnolia grandiflora</i> | | Water tupelo | <i>Nyssa aquatica</i> |
| | Sweetbay | <i>Magnolia virginiana</i> | Walnut | Black walnut | <i>Juglans nigra</i> |
| Maple, hard | Black maple | <i>Acer nigrum</i> | Willow | Black willow | <i>Salix nigra</i> |
| | Sugar maple | <i>Acer saccharum</i> | | Peachleaf willow | <i>Salix amygdaloides</i> |

diameter; must permit proper laying of floor and provide a serviceable floor; few restrictions on imperfections; must be possible to lay flooring properly

- Fourth grade—may contain all visual features, but must be possible to lay a serviceable floor, with some cutting

Combination grades of “Second and Better” and “Third and Better” are sometimes specified. There are also special grades based on color and species.

The standard thickness of MFMA hard maple, beech, and birch flooring is 20 mm (25/32 in.). Face widths are 38, 51, 57, and 83 mm (1-1/2, 2, 2-1/4, and 3-1/4 in.). Standard lengths are 610 mm (2 ft) and longer in First- and Second-grade flooring and 381 mm (1-1/4 ft) and longer in Third-grade flooring.

The Official Flooring Grading Rules of NOFMA cover oak (unfinished and prefinished), beech, birch, hard maple, ash, and hickory/pecan. Flooring grades are determined by the appearance of the face surface.

Oak is separated as red oak and white oak and by grain direction: plain sawn (all cuts), quartersawn (50% quartered character), rift sawn (75% rift character), and quarter/rift sawn (a combination). Oak flooring has four main grade separations—Clear, Select, No. 1 Common, and No. 2 Common. Clear is mostly heartwood and accepts a 10-mm (3/8-in.) strip of bright sapwood or an equivalent amount not more than 25 mm (1 in.) wide along the edge and a minimum number of character marks and discoloration, allowing for all natural heartwood color variations. Select allows all color variations of natural heartwood and sapwood

Table 6–4. Standard thickness values for rough and surfaced (S2S) hardwood lumber

| Rough (mm)(in.) | | Surfaced (mm)(in.) | |
|--------------------|---------|-----------------------|----------------|
| 10 | (3/8) | 5 | (3/16) |
| 13 | (1/2) | 8 | (5/16) |
| 16 | (5/8) | 9 | (7/16) |
| 19 | (3/4) | 14 | (9/16) |
| 25 | (1) | 21 | (13/16) |
| 32 | (1-1/4) | 27 | (1-1/16) |
| 38 | (1-1/2) | 33 | (1-5/16) |
| 44 | (1-3/4) | 38 | (1-1/2) |
| 51 | (2) | 44 | (1-3/4) |
| 63 | (2-1/2) | 57 | (2-1/4) |
| 76 | (3) | 70 | (2-3/4) |
| 89 | (3-1/2) | 83 | (3-1/4) |
| 102 | (4) | 95 | (3-3/4) |
| 114 | (4-1/2) | — ^a | — ^a |
| 127 | (5) | — ^a | — ^a |
| 140 | (5-1/2) | — ^a | — ^a |
| 152 | (6) | — ^a | — ^a |

^aFinished size not specified in rules. Thickness subject to special contract.

along with characters such as small knots, pinworm holes, and brown streaks. No. 1 Common contains prominent variations in coloration, which include heavy streaks, sticker stains, open checks, knots, and small knot holes that fill. No. 2 Common contains sound natural variation of the forest product and manufacturing imperfections to provide a serviceable floor.

Average lengths for unfinished oak grades are as follows:

| Grade | Standard packaging | Shorter packaging |
|--------------|--------------------|-------------------|
| Clear | 1.14 m (3-3/4 ft) | 1.07 m (3-1/2 ft) |
| Select | 0.99 m (3-1/4 ft) | 0.91 m (3 ft) |
| No. 1 Common | 0.84 m (2-3/4 ft) | 0.76 m (2-1/2 ft) |
| No. 2 Common | 0.69 m (2-1/4 ft) | 0.61 m (2 ft) |

Standard packaging refers to nominal 2.4-m (8-ft) pallets or nested bundles. Shorter packaging refers to nominal 2.1-m (7-ft) and shorter pallets or nested bundles.

Standard and special NOFMA grades for species other than oak are as follows:

| Species | Grade |
|------------------------------|---|
| Standard Grades | |
| Beech, birch, and hard maple | First, Second, Third, Second & Better, Third & Better |
| Hickory and pecan | First, Second, Third, Second & Better, Third & Better |
| Ash | Clear, Select, No. 1 Common, No. 2 Common |
| Special Grades | |
| Beech and birch | First Grade Red |
| Hard maple | First Grade White |
| Hickory and pecan | First Grade White, First Grade Red, Second Grade Red |

Standard thickness values for NOFMA tongue and groove flooring are 19, 13, 10 (3/4, 1/2, 3/8 in.), with 20 and 26 mm (25/32 and 33/32 in.) for maple flooring. Standard face widths are 38, 51, 57, and 83 mm (1-1/2, 2, 2-1/4, and 3-1/4 in.). Strips are random length from minimum 0.23 m to maximum 2.6 m (9 to 102 in.).

Lumber Species

Names used by the trade to describe commercial lumber in the United States are not always the same as names of trees adopted as official by the U.S. Forest Service. Table 6–3 shows the commercial name, the U.S Forest Service tree name, and the botanical name. United States agencies and associations that prepare rules for and supervise grading of hardwoods are given in Table 6–2.

Softwood Lumber

For many years, softwood lumber has demonstrated the versatility of wood by serving as a primary raw material for

construction and manufacture. In this role, softwood lumber has been produced in a wide variety of products from many different species. The first industry-sponsored grading rules (product descriptions) for softwoods, which were established before 1900, were comparatively simple because sawmills marketed their lumber locally and grades had only local significance. As new timber sources were developed and lumber was transported to distant points, each producing region continued to establish its own grading rules; thus, lumber from various regions differed in size, grade name, and allowable grade characteristics. When different species were graded under different rules and competed in the same consuming areas, confusion and dissatisfaction were inevitable.

To minimize unnecessary differences in the grading rules of softwood lumber and to improve and simplify these rules, a number of conferences were organized by the U.S. Department of Commerce from 1919 to 1925. These meetings were attended by representatives of lumber manufacturers, distributors, wholesalers, retailers, engineers, architects, and contractors. The result was a relative standardization of sizes, definitions, and procedures for deriving allowable design properties, formulated as a voluntary American Lumber Standard. This standard has been modified several times, including addition of hardwood species to the standard beginning in 1970. The current edition is the American Softwood Lumber Standard PS-20. Lumber cannot be graded as American Standard lumber unless the grade rules have been approved by the American Lumber Standard Committee (ALSC), Inc., Board of Review.

Softwood lumber is classified for market use by form of manufacture, species, and grade. For many products, the American Softwood Lumber Standard and the grading rules certified through it serve as a basic reference. For specific information on other products, reference must be made to grade rules, industry marketing aids, and trade journals.

Lumber Grades

Softwood lumber grades can be classified into three major categories of use: (a) yard lumber, (b) structural lumber, and (c) Factory and Shop lumber. Yard lumber and structural lumber relate principally to lumber expected to function as graded and sized after primary processing (sawing and planing). Factory and Shop refer to lumber that will undergo a number of further manufacturing steps and reach the consumer in a significantly different form.

Yard Lumber

Grading requirements of yard lumber are specifically related to the construction uses intended, and little or no further grading occurs once the piece leaves the sawmill. Yard lumber can be placed into two basic classifications, Select and Common. Select and Common lumber, as categorized here, encompass those lumber products in which appearance or utility is of primary importance; structural integrity, while sometimes important, is a secondary feature.

Select Lumber—Select lumber is generally non-stress-graded, but it forms a separate category because of the distinct importance of appearance in the grading process. Select lumber is intended for natural and paint finishes. This category of lumber includes lumber that has been machined to a pattern and S4S lumber. Secondary manufacture of these items is usually restricted to on-site fitting such as cutting to length and mitering. The Select category includes trim, siding, flooring, ceiling, paneling, casing, base, stepping, and finish boards.

Most Select lumber grades are generally described by letters and combinations of letters (B&BTR, C&BTR, C Select, D, D Select) or names (Superior, Prime, Supreme, Choice, Quality) depending upon the species and the grading rules under which the lumber is graded. (See list of commonly used lumber abbreviations at the end of this chapter.) The specifications FG (flat grain), VG (vertical grain), and MG (mixed grain) are offered as a purchase option for some select lumber products.

In cedar and redwood, there is a pronounced difference in color between heartwood and sapwood. Heartwood also has high natural resistance to decay, so some grades are denoted as “heart.” Because Select lumber grades emphasize the quality of one face, the reverse side may be lower in quality. Select lumber grades are not uniform across species and products, so certified grade rules for the species must be used for detailed reference.

Common Lumber—Common lumber is normally a non-stress-graded product. The grades of Common lumber are suitable for construction and utility purposes. Common lumber is generally separated into three to five different grades depending upon the species and grading rules involved. Grades may be described by number (No. 1, No. 2, No. 1 Common, No. 2 Common) or descriptive term (Select Merchantable, Construction, Standard).

Because there are differences in the inherent properties of various species and their corresponding names, the grades for different species are not always interchangeable. The top-grade boards (No. 1, No. 1 Common, Select Merchantable) are usually graded for serviceability, but appearance is also considered. These grades are used for such purposes as siding, cornice, shelving, and paneling. Features such as knots and knotholes are permitted to be larger and more frequent as the grade level becomes lower. Intermediate-grade boards are often used for such purposes as subfloors, roof and wall sheathing, and rough concrete work. The lower grade boards are selected for adequate usability, not appearance. They are used for roof and wall sheathing, subfloor, and rough concrete form work (Fig. 6-2).

Grading provisions for other non-stress-graded products vary by species, product, and applicable grading rules. For detailed descriptions, consult the appropriate grade rule for these products (see Table 6-5 for softwood grading organizations).

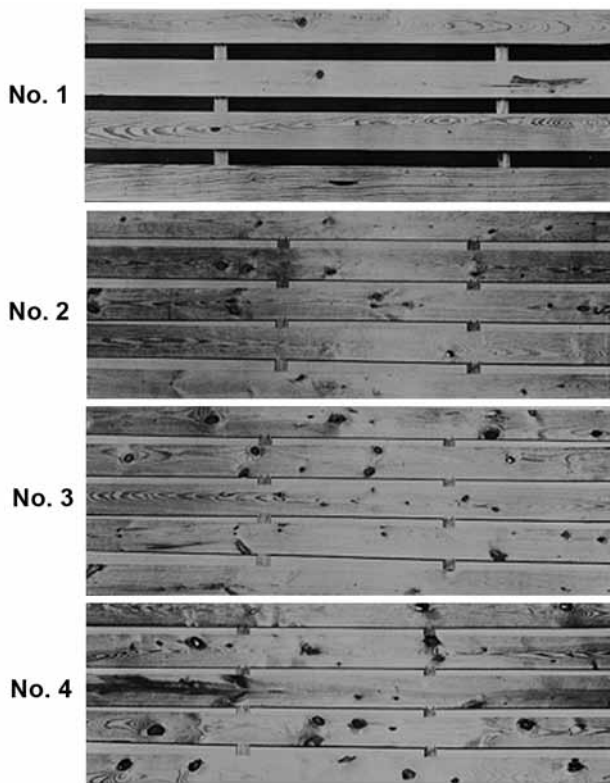


Figure 6–2. Typical examples of softwood boards in the lower grades.

Structural Lumber—Almost all softwood lumber standard 38 to 89 mm thick (nominal 2 to 4 in. thick, actual 1-1/2 to 3-1/2 in. thick) is produced as dimension lumber. Dimension lumber is stress graded and assigned allowable properties under the National Grading Rule, a part of the American Softwood Lumber Standard. For dimension lumber, a single set of grade names and descriptions is used throughout the United States, although the allowable properties vary with species. Timbers (lumber standard 114 mm (nominal 5 in.) or more in least dimension) are also structurally graded under ALSC procedures. Unlike grade descriptions for dimension lumber, grade descriptions for structural timbers are not standardized across species. For most species, timber grades are classified according to intended use. Beams and stringers are members standard 114 mm (nominal 5 in.) or more in thickness with a width more than 38 mm (nominal 2 in.) greater than the thickness. Beams and stringers are primarily used to resist bending stresses, and the grade description of some timber grades for the middle third of the length of the beam is more stringent than that for the outer two-thirds. Posts and timbers are members standard 114 by 114 mm (nominal 5 by 5 in.) and larger, where the width is not more than 38 mm (nominal 2 in.) greater than the thickness. Post and timbers are primarily used to resist axial stresses. Structural timbers of Southern Pine are graded without regard to anticipated use, as with dimension lumber.

Other stress-graded products include decking and some boards. Stress-graded lumber may be graded visually or

mechanically. Stress grades and the National Grading Rule are discussed in Chapter 6.

Structural Laminations—Structural laminating grades describe the characteristics used to segregate lumber to be used in structural glued-laminated (glulam) timbers. Generally, allowable properties are not assigned separately to laminating grades; rather, the rules for laminating grades are based on the expected effect of that grade of lamination on the combined glulam timber.

There are two kinds of graded material: visually graded and E-rated. Visually graded material is graded according to one of three sets of grading rules: (1) the first set is based on the grading rules certified as meeting the requirements of the American Softwood Lumber Standard with additional requirements for laminating; (2) the second set involves laminating grades typically used for visually graded western species and includes three basic categories (L1, L2, L3); and (3) the third set includes special requirements for tension members and outer tension laminations on bending members. The visual grades have provisions for dense, close-grain, medium-grain, or coarsegrain lumber.

The E-rated grades are categorized by a combination of visual grading criteria and lumber stiffness. These grades are expressed in terms of the size of maximum edge characteristic permitted (as a fraction of the width) along with a specified long-span modulus of elasticity (for example, 1/6–2.2E).

Radius-Edged Decking—Radius-edged decking is another substantial softwood lumber product. Radius-edged decking is intended for flatwise use and has oversized eased edges of a particular radius. Most often radius-edged decking is produced as 25- or 38-mm- (nominal 5/4- or 2-in.-, actual 1- or 1-1/2-in.-) thick by 140-mm- (nominal 4- to 6-in.-, actual 3-1/2- to 5-1/2-in.-) wide pieces of lumber 2.4 to 4.9 m (8 to 16 ft) in length. The standard radius for 25-mm-thick radius-edged decking product is 6.4 mm (1/4 in.), and 9.5 mm (3/8 in.) for 38-mm-thick decking. Decking is usually separated into a minimum of two grades, most commonly Premium and Standard.

Factory and Shop Lumber

A wide variety of species, grades, and sizes of softwood lumber is supplied to industrial accounts for cutting to specific smaller sizes, which become integral parts of other products. In the secondary manufacturing process, grade descriptions, sizes, and often the entire appearance of the wood piece are changed. Thus, for Factory and Shop lumber, the role of the grading process is to reflect as accurately as possible the yield to be obtained in the subsequent cutting operation. Typical of lumber for secondary manufacture are the factory grades, industrial clears, box lumber, moulding stock, and ladder stock. The variety of species available for these purposes has led to a variety of grade names and grade definitions. The following sections briefly outline some of the more common classifications. For details, reference must

Table 6–5. Organizations promulgating softwood grades

| Name and address | Species covered by grading rules |
|--|--|
| Cedar Shingle & Shake Bureau 515 116th Avenue NE, Suite 275 Bellevue, WA 98004–5294 | Western redcedar (shingles and shakes) |
| National Hardwood Lumber Association P.O. Box 34518 Memphis, TN 38184–0518 | Baldcypress, eastern redcedar |
| National Lumber Grades Authority ^a 406 First Capital Place 960 Quamside Drive New Westminster, BC, Canada V3M6G2 | Northern white-cedar, western redcedar, yellow-cedar, alpine fir, amabilis fir, balsam fir, Douglas-fir, grand fir, eastern hemlock, western hemlock, western larch, eastern white pine, jack pine, lodgepole pine, ponderosa pine, red pine, western white pine, black spruce, Sitka spruce, red spruce, Engelmann spruce, white spruce, tamarack, aspen, black cottonwood, balsam poplar, red alder, white birch |
| Northeastern Lumber Manufacturers Association, Inc. ^a 272 Tuttle Road, P.O. Box 87A Cumberland Center, ME 04021 | Balsam fir, eastern white pine, red pine, eastern hemlock, black spruce, white spruce, red spruce, pitch pine, tamarack, jack pine, northern white cedar, aspen, mixed maple, beech, birch, hickory, mixed oaks, yellow poplar |
| Northern Softwood Lumber Bureau ^a 272 Tuttle Road, P.O. Box 87A Cumberland Center, ME 04021 | Eastern white pine, jack pine, red pine, pitch pine, eastern spruce (red, white, and black), balsam fir, eastern hemlock, tamarack, eastern cottonwood, aspen yellow poplar |
| Redwood Inspection Service ^a 405 Enfrente Drive, Suite 200 Novato, CA 94949 | Redwood |
| Southern Cypress Manufacturers Association 400 Penn Center Boulevard Suite 530 Pittsburgh, PA 15235 | Baldcypress |
| Southern Pine Inspection Bureau ^a 4709 Scenic Highway Pensacola, FL 32504 | Longleaf pine, slash pine, shortleaf pine, loblolly pine, Virginia pine, pond pine, sand pine, baldcypress |
| West Coast Lumber Inspection Bureau ^a Box 23145 6980 SW. Varns Road Portland, OR 97223 | Douglas-fir, western hemlock, western redcedar, incense-cedar, Port-Orford-cedar, yellow-cedar, western true firs, mountain hemlock, Sitka spruce, western larch |
| Western Wood Products Association ^a Yeon Building, 522 SW Fifth Avenue Portland, OR 97204–2122 | Ponderosa pine, western (Idaho) white pine, Douglas-fir, sugar pine, western true firs, western larch, Engelmann spruce, incense-cedar, western hemlock, lodgepole pine, western redcedar, mountain hemlock, red alder, aspen, subalpine fir, Sitka spruce, Port-Orford cedar |

^aPublishes grading rules certified by the Board of Review of the American Lumber Standard Committee as conforming to the American Softwood Lumber Standard PS–20.

be made to industry sources, such as certified grading rules. Availability and grade designation often vary by region and species.

Factory (Shop) Grades—Traditionally, softwood lumber used for cuttings has been called Factory or Shop. This lumber forms the basic raw material for many secondary manufacturing operations. Some grading rules refer to these grades as Factory, while others refer to them as Shop. All impose a somewhat similar nomenclature in the grade structure. Shop lumber is graded on the basis of characteristics that affect its use for general cut-up purposes or on the basis of size of cutting, such as for sash and doors. Factory Select and Select Shop are typical high grades, followed by No. 1 Shop, No. 2 Shop, and No. 3 Shop.

Grade characteristics of boards are influenced by the width, length, and thickness of the basic piece and are based on the amount of high-quality material that can be removed by cutting. Typically, Factory Select and Select Shop lumber would be required to contain 70% of cuttings of specified size, clear on both sides. No. 1 Shop would be required to have 50% cuttings and No. 2 Shop, 33-1/3%. Because of different characteristics assigned to grades with similar nomenclature, the grades of Factory and Shop lumber must be referenced to the appropriate certified grading rules.

Industrial Clears—These grades are used for trim, cabinet stock, garage door stock, and other product components where excellent appearance, mechanical and physical properties, and finishing characteristics are important. The principal grades are B&BTR, C, and D Industrial. Grading is primarily based on the best face, although the influence of edge characteristics is important and varies depending upon piece width and thickness. In redwood, the Industrial Clear All Heart grade includes an “all heart” requirement for decay resistance in the manufacture of cooling towers, tanks, pipe, and similar products.

Moulding, Ladder, Pole, Tank, and Pencil Stock—Within producing regions, grading rules delineate the requirements for a variety of lumber classes oriented to specific consumer products. Custom and the characteristics of the wood supply have led to different grade descriptions and terminology. For example, in West Coast species, the ladder industry can choose from one “ladder and pole stock” grade plus two ladder rail grades and one ladder rail stock grade. In Southern Pine, ladder stock is available as Select and Industrial. Moulding stock, tank stock, pole stock, stave stock, stadium seat stock, box lumber, and pencil stock are other typical classes oriented to the final product. Some product classes have only one grade level; a few offer two or three levels. Special features of these grades may include a restriction on sapwood related to desired decay resistance, specific requirements for slope of grain and growth ring orientation for high-stress use such as ladders, and particular cutting requirements as in pencil stock. All references to these grades should be made directly to current certified grading rules.

Lumber Manufacture

Size

Lumber length is recorded in actual dimensions, whereas width and thickness are traditionally recorded in “nominal” dimensions—actual dimensions are somewhat less.

Softwood lumber is manufactured in length multiples of 305 mm (1 ft) as specified in various grading rules. In practice, 610-mm (2-ft) multiples (in even numbers) are common for most construction lumber. Width of softwood lumber varies, commonly from standard 38 to 387 mm (nominal 2 to 16 in.). The thickness of lumber can be generally categorized as follows:

- Boards—lumber less than standard 38 mm (nominal 2 in.) in thickness
- Dimension—lumber from standard 38 mm (nominal 2 in.) to, but not including, 114 mm (nominal 5 in.) in thickness
- Timbers—lumber standard 114 mm (nominal 5 in.) or more in thickness in least dimension

To standardize and clarify nominal to actual sizes, the American Softwood Lumber Standard PS–20 specifies the actual thickness and width for lumber that falls under the standard. The standard sizes for yard and structural lumber are given in Table 6–6. Timbers are usually surfaced while “green” (unseasoned); however, dry sizes are also given.

Because dimension lumber and boards of some species may be surfaced green or dry at the prerogative of the manufacturer, both green and dry standard sizes are given. The sizes are such that a piece of green lumber, surfaced to the standard green size, will shrink to approximately the standard dry size as it dries to about 15% moisture content. The definition of dry boards and dimension is lumber that has been seasoned or dried to a maximum moisture content of 19%. The definition for dry timbers of the various species is found in the certified grading rules. Lumber may also be designated as kiln dried (KD), meaning the lumber has been seasoned in a chamber to a predetermined moisture content by applying heat.

Factory and Shop lumber for remanufacture is offered in specified sizes to fit end-product requirements. Factory (Shop) grades for general cuttings are offered in thickness from standard 19 to 89 mm (nominal 1 to 4 in.). Thicknesses of door cuttings start at 29 mm (nominal 1-3/8 in.). Cuttings are of various lengths and widths. Laminating stock is sometimes offered oversize, compared with standard dimension sizes, to permit resurfacing prior to laminating. Industrial Clears can be offered rough or surfaced in a variety of sizes, starting from standard 38 mm (nominal 2 in.) and thinner and as narrow as standard 64 mm (nominal 3 in.). Sizes for special product grades such as moulding stock and ladder stock are specified in appropriate grading rules or handled by purchase agreements.

Table 6–6. American Standard Lumber sizes for yard and structural lumber for construction

| Item | Thickness | | | | | Face width | | | | | |
|---------|-------------|-----------------|------------------|--------------|------------------|------------|-----------------|------------------|--------------|------------------|----------|
| | Nominal | Minimum dressed | | | | Nominal | Minimum dressed | | | | |
| | | Dry | Green | | Dry | | Green | | | | |
| (in.) | (mm) | (in.) | (mm) | (in.) | (in.) | (mm) | (in.) | (mm) | (in.) | | |
| Boards | 1 | 19 | (3/4) | 20 | (25/32) | 2 | 38 | (1-1/2) | 40 | (1-9/16) | |
| | 1-1/4 | 25 | (1) | 26 | (1-1/32) | 3 | 64 | (2-1/2) | 65 | (2-9/16) | |
| | 1-1/2 | 32 | (1-1/4) | 33 | (1-9/32) | 4 | 89 | (3-1/2) | 90 | (3-9/16) | |
| | | | | | | 5 | 114 | (4-1/2) | 117 | (4-5/8) | |
| | | | | | | 6 | 140 | (5-1/2) | 143 | (5-5/8) | |
| | | | | | | 7 | 165 | (6-1/2) | 168 | (6-5/8) | |
| | | | | | | 8 | 184 | (7-1/4) | 190 | (7-1/2) | |
| | | | | | | 9 | 210 | (8-1/4) | 216 | (8-1/2) | |
| | | | | | | 10 | 235 | (9-1/4) | 241 | (9-1/2) | |
| | | | | | | 11 | 260 | (10-1/4) | 267 | (10-1/2) | |
| | | | | | | 12 | 286 | (11-1/4) | 292 | (11-1/2) | |
| | | | | | | 14 | 337 | (13-1/4) | 343 | (13-1/2) | |
| | | | | | | 16 | 387 | (15-1/4) | 394 | (15-1/2) | |
| | Dimension | 2 | 38 | (1-1/2) | 40 | (1-9/16) | 2 | 38 | (1-1/2) | 40 | (1-9/16) |
| | | 2-1/2 | 51 | (2) | 52 | (2-1/16) | 3 | 64 | (2-1/2) | 65 | (2-9/16) |
| | | 3 | 64 | (2-1/2) | 65 | (2-9/16) | 4 | 89 | (3-1/2) | 90 | (3-9/16) |
| 3-1/2 | | 76 | (3) | 78 | (3-1/16) | 5 | 114 | (4-1/2) | 117 | (4-5/8) | |
| 4 | | 89 | (3-1/2) | 90 | (3-9/16) | 6 | 140 | (5-1/2) | 143 | (5-5/8) | |
| 4-1/2 | | 102 | (4) | 103 | (4-1/16) | 8 | 184 | (7-1/4) | 190 | (7-1/2) | |
| | | | | | | 10 | 235 | (9-1/4) | 241 | (9-1/2) | |
| | | | | | | 12 | 286 | (11-1/4) | 292 | (11-1/2) | |
| | | | | | | 14 | 337 | (13-1/4) | 343 | (13-1/2) | |
| | | | | | | 16 | 387 | (15-1/4) | 394 | (15-1/2) | |
| Timbers | 5 & 6 thick | 13 mm off | (1/2 in. off) | 13 mm off | (1/2 in. off) | 5 & 6 wide | 13 mm off | (1/2 in. off) | 13 mm off | (1/2 in. off) | |
| | 7–15 thick | 19 mm off | (3/4 in. off) | 13 mm off | (1/2 in. off) | 7–15 wide | 19 mm off | (3/4 in. off) | 13 mm off | (1/2 in. off) | |
| | ≥ 16 thick | 25 mm off | (1 in. off) | 13 mm off | (1/2 in. off) | ≥ 16 wide | 25 mm off | (1 in. off) | 13 mm off | (1/2 in. off) | |

Surfacing

Lumber can be produced either rough or surfaced (dressed). Rough lumber has surface imperfections caused by the primary sawing operations. It may be greater than target size by variable amounts in both thickness and width, depending upon the type of sawmill equipment. Rough lumber serves as a raw material for further manufacture and also for some decorative purposes. A roughsawn surface is common in post and timber products.

Surfaced lumber has been surfaced by a machine on one side (S1S), two sides (S2S), one edge (S1E), two edges (S2E), or combinations of sides and edges (S1S1E, S2S1E, S1S2, S4S). Lumber is surfaced to attain smoothness of surface and uniformity of size.

Imperfections or blemishes defined in the grading rules and caused by machining are classified as “manufacturing imperfections.” For example, chipped and torn grain are surface irregularities in which surface fibers have been torn out by the surfacing operation. Chipped grain is a “barely perceptible” characteristic, while torn grain is classified by depth. Raised grain, skip, machine burn and gouge, chip marks, and wavy surfacing are other manufacturing imperfections. Manufacturing imperfections are defined in the

American Softwood Lumber Standard and further detailed in the grading rules. Classifications of manufacturing imperfections (combinations of imperfections allowed) are established in the rules as Standard A, Standard B, and so on. For example, Standard A admits very light torn grain, occasional very light chip marks, and very slight knife marks. These classifications are used as part of the grade rule description of some lumber products to specify the allowable surface quality.

Patterns

Lumber that has been matched, shiplapped, or otherwise patterned, in addition to being surfaced, is often classified as “worked lumber.” Figure 6–3 shows typical patterns.

Softwood Lumber Species

The names of lumber species adopted by the trade as standard may vary from the names of trees adopted as official by the U.S. Forest Service. Table 6–7 shows the American Softwood Lumber Standard commercial names for lumber, the U.S. Forest Service tree names, and the botanical names. Some softwood species are marketed primarily in combinations. Designations such as Southern Pine and Hem–Fir represent typical combinations. Grading rule agencies

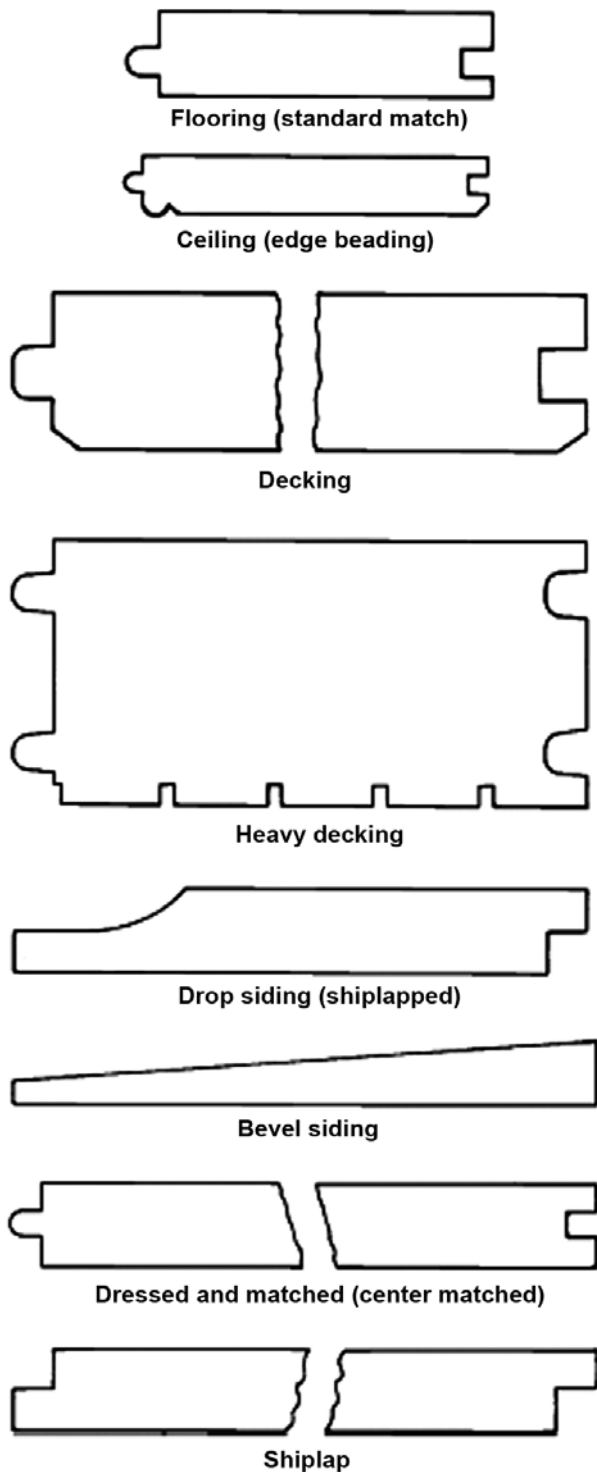


Figure 6-3. Typical patterns of worked lumber.

(Table 6-5) should be contacted for questions regarding combination names and species not listed in Table 6-7. Species groups are discussed further in Chapter 7.

Softwood Lumber Grading

Most lumber is graded under the supervision of inspection bureaus and grading agencies. These organizations supervise lumber mill grading and provide reinspection services

to resolve disputes concerning lumber shipments. Some of these agencies also write grading rules that reflect the species and products in the geographic regions they represent. These grading rules follow the American Softwood Lumber Standard (PS-20). This is important because it provides for recognized uniform grading procedures. Names and addresses of rules-writing organizations in the United States and the species with which they are concerned are listed in Table 6-5. Canadian softwood lumber imported into the United States and graded by inspection agencies in Canada also follows the PS-20 standard. (Names and addresses of accredited Canadian grading agencies may be obtained from the American Lumber Standard Committee, P.O. Box 210, Germantown, MD 20874; email: alsc@alsc.org; www.alsc.org.)

Purchase of Lumber

After primary manufacture, most lumber products are marketed through wholesalers to remanufacturing plants or retail outlets. Because of the extremely wide variety of lumber products, wholesaling is very specialized—some organizations deal with only a limited number of species or products. Where the primary manufacturer can readily identify the customers, direct sales may be made. Primary manufacturers often sell directly to large retail-chain contractors, manufacturers of mobile and modular housing, and truss fabricators.

Some primary manufacturers and wholesalers set up distribution yards in lumber-consuming areas to distribute both hardwood and softwood products more effectively. Retail yards draw inventory from distribution yards and, in wood-producing areas, from local lumber producers. The wide range of grades and species covered in the grade rules may not be readily available in most retail outlets.

Transportation is a vital factor in lumber distribution. Often, the lumber shipped by water is green because weight is not a major factor in this type of shipping. On the other hand, lumber reaching the East Coast from the Pacific Coast by rail is usually kiln-dried because rail shipping rates are based on weight. A shorter rail haul places southern and northeastern species in a favorable economic position in regard to shipping costs in this market.

Changing transportation costs have influenced shifts in market distribution of species and products. Trucks have become a major factor in lumber transport for regional remanufacture plants, for retail supply from distribution yards, and for much construction lumber distribution.

The increased production capacity of foreign hardwood and softwood manufacturing and the availability of water transport have brought foreign lumber products to the U.S. market, particularly in coastal areas.

Retail Yard Inventory

Small retail yards throughout the United States carry softwoods for construction purposes and often carry small

Table 6–7. Nomenclature of principal commercial softwood lumber

| Commercial species or species group names under American Softwood Lumber Standard | Tree name used in this handbook | Botanical name |
|---|---------------------------------|--|
| Cedar | | |
| Alaska | yellow-cedar | <i>Chamaecyparis nootkatensis</i> |
| Eastern red | eastern redcedar | <i>Juniperus virginiana</i> |
| Incense | incense-cedar | <i>Libocedrus decurrens</i> |
| Northern white | northern white-cedar | <i>Thuja occidentalis</i> |
| Port Orford | Port-Orford-cedar | <i>Chamaecyparis lawsoniana</i> |
| Southern white | Atlantic white-cedar | <i>Chamaecyparis thyoides</i> |
| Western red | western redcedar | <i>Thuja plicata</i> |
| Cypress | | |
| Baldcypress | baldcypress | <i>Taxodium distichum</i> |
| Pond cypress | pond cypress | <i>Taxodium distichum</i> var. <i>nutans</i> |
| Fir | | |
| Alpine | subalpine fir (alpine fir) | <i>Abies lasiocarpa</i> |
| Balsam | balsam fir | <i>Abies balsamea</i> |
| California red | California red fir | <i>Abies magnifica</i> |
| Douglas Fir | Douglas-fir | <i>Pseudotsuga menziesii</i> |
| Fraser | Fraser fir | <i>Abies fraseri</i> |
| Grand | grand fir | <i>Abies grandis</i> |
| Noble Fir | noble fir | <i>Abies procera</i> |
| Pacific Grand | Pacific silver fir | <i>Abies amabilis</i> |
| White | white fir | <i>Abies concolor</i> |
| Hemlock | | |
| Carolina | Carolina hemlock | <i>Tsuga caroliniana</i> |
| Eastern | eastern hemlock | <i>Tsuga canadensis</i> |
| Mountain | mountain hemlock | <i>Tsuga mertensiana</i> |
| Western | western hemlock | <i>Tsuga heterophylla</i> |
| Juniper | | |
| Western | alligator juniper | <i>Juniperus deppeana</i> |
| | Rocky Mountain juniper | <i>Juniperus scopulorum</i> |
| | Utah juniper | <i>Juniperus osteosperma</i> |
| | western juniper | <i>Juniperus occidentalis</i> |
| Larch | | |
| Western | western larch | <i>Larix occidentalis</i> |
| Pine | | |
| Bishop | bishop pine | <i>Pinus muricata</i> |
| Coulter | Coulter pine | <i>Pinus coulteri</i> |
| Digger | Digger pine | <i>Pinus sabibiana</i> |
| Knobcone | knobcone pine | <i>Pinus attenuata</i> |
| Idaho white | Western white pine | <i>Pinus monticola</i> |
| Jack | jack pine | <i>Pinus banksiana</i> |
| Jeffrey | Jeffrey pine | <i>Pinus jeffreyi</i> |
| Limber | limber pine | <i>Pinus flexilis</i> |
| Lodgepole | lodgepole pine | <i>Pinus contorta</i> |
| Longleaf | longleaf pine | <i>Pinus palustris</i> |
| | slash pine | <i>Pinus elliottii</i> |
| Northern white | eastern white pine | <i>Pinus strobus</i> |
| Norway | red pine | <i>Pinus resinosa</i> |
| Pitch | pitch pine | <i>Pinus rigida</i> |
| Ponderosa | ponderosa pine | <i>Pinus ponderosa</i> |
| Southern Pine Major | loblolly pine | <i>Pinus taeda</i> |
| | longleaf pine | <i>Pinus palustris</i> |
| | shortleaf pine | <i>Pinus echinata</i> |
| | slash pine | <i>Pinus elliottii</i> |
| Southern Pine Minor | pond pine | <i>Pinus serotina</i> |
| | sand pine | <i>Pinus clausa</i> |
| | spruce pine | <i>Pinus glabra</i> |
| | Virginia pine | <i>Pinus virginiana</i> |
| Southern Pine Mixed | loblolly pine | <i>Pinus taeda</i> |
| | longleaf pine | <i>Pinus palustris</i> |

Table 6–7. Nomenclature of principal commercial softwood lumber—con.

| Commercial species or species group names under American Softwood Lumber Standard | Tree name used in this handbook | Botanical name |
|---|---------------------------------|-----------------------------------|
| | pond pine | <i>Pinus serotina</i> |
| | shortleaf pine | <i>Pinus echinata</i> |
| | slash pine | <i>Pinus elliottii</i> |
| | Virginia pine | <i>Pinus virginiana</i> |
| Radiata/Monterey Pine | Monterey pine | <i>Pinus radiata</i> |
| Sugar | sugar pine | <i>Pinus lambertiana</i> |
| Whitebark | whitebark pine | <i>Pinus albicaulis</i> |
| Redwood | | |
| Redwood | redwood | <i>Sequoia sempervirens</i> |
| Spruce | | |
| Blue | blue spruce | <i>Picea pungens</i> |
| Eastern | black spruce | <i>Picea mariana</i> |
| | red spruce | <i>Picea rubens</i> |
| | white spruce | <i>Picea glauca</i> |
| Engelmann | Engelmann spruce | <i>Picea engelmannii</i> |
| Sitka | Sitka spruce | <i>Picea sitchensis</i> |
| Tamarack | | |
| Tamarack | tamarack | <i>Larix laricina</i> |
| Yew | | |
| Pacific | Pacific yew | <i>Taxus brevifolia</i> |
| Coast Species | Douglas-fir | <i>Pseudotsuga menziesii</i> |
| | western larch | <i>Larix occidentalis</i> |
| Eastern Softwoods | black spruce | <i>Picea mariana</i> |
| | red spruce | <i>Picea rubens</i> |
| | white spruce | <i>Picea glauca</i> |
| | balsam fir | <i>Abies balsamea</i> |
| | eastern white pine | <i>Pinus strobus</i> |
| | jack pine | <i>Pinus banksiana</i> |
| | pitch pine | <i>Pinus rigida</i> |
| | red pine | <i>Pinus resinosa</i> |
| | eastern hemlock | <i>Tsuga canadensis</i> |
| Hem–Fir | tamarack | <i>Larix occidentalis</i> |
| | western hemlock | <i>Tsuga heterophylla</i> |
| | California red fir | <i>Abies magnifica</i> |
| | grand fir | <i>Abies grandis</i> |
| | noble fir | <i>Abies procera</i> |
| | Pacific silver fir | <i>Abies amabilis</i> |
| | white fir | <i>Abies concolor</i> |
| Hem–Fir (North) | western hemlock | <i>Tsuga heterophylla</i> |
| | Pacific silver fir | <i>Abies amabilis</i> |
| Northern Pine | jack pine | <i>Pinus banksiana</i> |
| | pitch pine | <i>Pinus rigida</i> |
| | red pine | <i>Pinus resinosa</i> |
| North Species | northern white cedar | <i>Thuja occidentalis</i> |
| | western redcedar | <i>Thuja plicata</i> |
| | yellow-cedar | <i>Chamaecyparis nootkatensis</i> |
| | eastern hemlock | <i>Tsuga canadensis</i> |
| | western hemlock | <i>Tsuga heterophylla</i> |
| | Douglas-fir | <i>Pseudotsuga menziesii</i> |
| | balsam fir | <i>Abies balsamea</i> |
| | grand fir | <i>Abies grandis</i> |
| | Pacific silver fir | <i>Abies amabilis</i> |
| | subalpine (alpine) fir | <i>Abies lasiocarpa</i> |
| | western larch | <i>Larix occidentalis</i> |
| | tamarack | <i>Larix laricina</i> |
| | eastern white pine | <i>Pinus strobus</i> |
| | jack pine | <i>Pinus banksiana</i> |
| | lodgepole pine | <i>Pinus contorta</i> |
| | ponderosa pine | <i>Pinus ponderosa</i> |
| | red pine | <i>Pinus resinosa</i> |
| | western white pine | <i>Pinus monticola</i> |
| | whitebark pine | <i>Pinus albicaulis</i> |

Table 6–7. Nomenclature of principal commercial softwood lumber—con.

| Commercial species or species group names under American Softwood Lumber Standard | Tree name used in this handbook | Botanical name |
|---|---------------------------------|-----------------------------------|
| | black spruce | <i>Picea mariana</i> |
| | Engelmann spruce | <i>Picea engelmannii</i> |
| | red spruce | <i>Picea rubens</i> |
| | Sitka spruce | <i>Picea sitchensis</i> |
| | bigtooth aspen | <i>Populus grandidentata</i> |
| | quaking aspen | <i>Populus tremuloides</i> |
| | black cottonwood | <i>Populus trichocarpa</i> |
| | balsam poplar | <i>Populus balsamifera</i> |
| Southern Pine | loblolly pine | <i>Pinus taeda</i> |
| | longleaf pine | <i>Pinus palustris</i> |
| | shortleaf pine | <i>Pinus echinata</i> |
| | slash pine | <i>Pinus elliotii</i> |
| Spruce–Pine–Fir | black spruce | <i>Picea mariana</i> |
| | Engelmann spruce | <i>Picea engelmannii</i> |
| | red spruce | <i>Picea rubens</i> |
| | balsam fir | <i>Abies balsamea</i> |
| | subalpine (alpine) fir | <i>Abies lasiocarpa</i> |
| | jack pine | <i>Pinus banksiana</i> |
| | lodgepole pine | <i>Pinus contorta</i> |
| Spruce–Pine–Fir (South) | black spruce | <i>Picea mariana</i> |
| | Engelmann spruce | <i>Picea engelmannii</i> |
| | red spruce | <i>Picea rubens</i> |
| | Sitka spruce | <i>Picea sitchensis</i> |
| | white spruce | <i>Picea glauca</i> |
| | balsam fir | <i>Abies balsamea</i> |
| | jack pine | <i>Pinus banksiana</i> |
| | lodgepole pine | <i>Pinus contorta</i> |
| | red pine | <i>Pinus resinosa</i> |
| Western Cedars | incense-cedar | <i>Libocedrus decurrens</i> |
| | western redcedar | <i>Thuja plicata</i> |
| | Port-Orford-cedar | <i>Chamaecyparis lawsoniana</i> |
| | yellow-cedar | <i>Chamaecyparis nootkatensis</i> |
| Western Cedar (North) | western redcedar | <i>Thuja plicata</i> |
| | yellow-cedar | <i>Chamaecyparis nootkatensis</i> |
| Western Woods | Douglas-fir | <i>Pseudotsuga menziesii</i> |
| | California red fir | <i>Abies magnifica</i> |
| | grand fir | <i>Abies grandis</i> |
| | noble fir | <i>Abies procera</i> |
| | Pacific silver fir | <i>Abies amabilis</i> |
| | subalpine fir | <i>Abies lasiocarpa</i> |
| | white fir | <i>Abies concolor</i> |
| Hemlock | mountain | <i>Tsuga mertensiana</i> |
| | western hemlock | <i>Tsuga heterophylla</i> |
| | western larch | <i>Larix occidentalis</i> |
| | Engelmann spruce | <i>Picea engelmannii</i> |
| | Sitka spruce | <i>Picea sitchensis</i> |
| | lodgepole pine | <i>Pinus contorta</i> |
| | ponderosa pine | <i>Pinus ponderosa</i> |
| | sugar pine | <i>Pinus lambertiana</i> |
| | western white pine | <i>Pinus monticola</i> |
| White Woods | California red fir | <i>Abies magnifica</i> |
| | grand fir | <i>Abies grandis</i> |
| | noble fir | <i>Abies procera</i> |
| | Pacific silver fir | <i>Abies amabilis</i> |
| | subalpine fir | <i>Abies lasiocarpa</i> |
| | white fir | <i>Abies concolor</i> |
| | mountain hemlock | <i>Tsuga mertensiana</i> |
| | western hemlock | <i>Tsuga heterophylla</i> |
| | Engelmann spruce | <i>Picea engelmannii</i> |
| | Sitka spruce | <i>Picea sitchensis</i> |
| | lodgepole pine | <i>Pinus contorta</i> |
| | ponderosa pine | <i>Pinus ponderosa</i> |
| | sugar pine | <i>Pinus lambertiana</i> |
| | western white pine | <i>Pinus monticola</i> |

stocks of one or two hardwoods in grades suitable for finishing or cabinetwork. Special orders must be made for other hardwoods. Trim items such as moulding in either softwood or hardwood are available cut to standard size and pattern. Millwork plants usually make ready-for-installation cabinets, and retail yards carry or catalog many common styles and sizes. Hardwood flooring is available to the buyer only in standard patterns. Most retail yards carry stress grades of lumber.

The assortment of species in general construction items carried by retail yards depends to a great extent upon geographic location, and both transportation costs and tradition are important factors. Retail yards within, or close to, a major lumber-producing region commonly emphasize local timber. For example, a local retail yard on the Pacific Northwest Coast may stock only green Douglas Fir and cedar in dimension grades, dry pine and hemlock in boards and moulding, and assorted special items such as redwood posts, cedar shingles and shakes, and rough cedar siding. The only hardwoods may be walnut and “Philippine mahogany” (the common market name encompassing many species, including tanguile, red meranti, and white lauan). Retail yards located farther from a major softwood supply, such as in the Midwest, may draw from several growing areas and may stock spruce and Southern Pine, for example. Because they are located in a major hardwood production area, these yards may stock, or have available to them, a different and wider variety of hardwoods.

Geography has less influence where consumer demands are more specific. For example, where long construction lumber (6 to 8 m (20 to 26 ft)) is required, West Coast species are often marketed because the height of the trees in several species makes long lengths a practical market item. Ease of preservative treatability makes treated Southern Pine construction lumber available in a wide geographic area.

Structural Lumber for Construction

Dimension lumber is the principal stress-graded lumber available in a retail yard. It is primarily framing lumber for joists, rafters, and studs. Strength, stiffness, and uniformity of size are essential requirements. Dimension lumber is stocked in almost all yards, frequently in only one or two of the general purpose construction woods such as pine, fir, hemlock, or spruce. Standard 38- by 89-mm (nominal 2- by 4-in.) and wider dimension lumber is found in Select Structural, No. 1, No. 2, and No. 3 grades. Standard 38- by 89-mm (nominal 2- by 4-in.) dimension lumber may also be available as Construction, Standard, Utility, and Stud grades. Stud grade is also available in wider widths.

Dimension lumber is often found in standard 38-, 89-, 140-, 184-, 235-, and 286-mm (nominal 2-, 4-, 6-, 8-, 10-, and 12-in.) widths and 2.4- to 5.5-m (8- to 18-ft) lengths in multiples of 0.6 m (2 ft). Dimension lumber formed by structural end-jointing procedures may be available. Dimension lumber thicker than standard 38 mm (nominal 2 in.) and

longer than 5.5 m (18 ft) may not be commonly available in many retail yards.

Other stress-graded products generally available are posts and timbers; some beams and stringers may also be in stock. Typical grades in these products are Select Structural, No. 1, and No. 2.

Yard Lumber for Construction

Boards are the most common non-stress-graded general purpose construction lumber in the retail yard. Boards are stocked in one or more species, usually in standard 19-mm (nominal 1-in.) thickness. Common widths are standard 38, 64, 89, 140, 184, 235, and 286 mm (nominal 2, 3, 4, 6, 8, 10, and 12 in.). Grades generally available in retail yards are No. 1 Common, No. 2 Common, and No. 3 Common (Construction, Standard, No. 1, No. 2, etc.). Boards are sold square edged, dressed (surfaced) and matched (tongued and grooved), or with a shiplapped joint. Boards formed by end-jointing of shorter sections may constitute an appreciable portion of the inventory.

Select Lumber

Completion of a construction project usually depends on the availability of lumber items in finished or semi-finished form. The following items often may be stocked in only a few species, finishes, or sizes depending on the lumber yard.

Finish—Finish boards usually are available in a local yard in one or two species, principally in grade C&BTR. Cedar and redwood have different grade designations: grades such as Clear Heart, A, or B are used in cedar; Clear All Heart, Clear, and B grade are typical in redwood. Finish boards are usually standard 19 mm (nominal 1 in.) thick, surfaced on two sides to 19 mm (nominal 1 in.); 38- to 286-mm (nominal 2- to 12-in.) widths are usually stocked, in even increments.

Siding—Siding is specifically intended to cover exterior walls. Beveled siding is ordinarily stocked in white pine, ponderosa pine, western redcedar, cypress, or redwood. Drop siding, also known as rustic or barn siding, is usually stocked in the same species as is beveled siding. Siding may be stocked as B&BTR or C&BTR except in cedar, where Clear, A, and B grades may be available, and redwood, where Clear All Heart, Clear, and B grades may be found. Vertical grain (VG) is sometimes part of the grade designation. Drop siding is also sometimes stocked in C and D grades of Southern Pine, Douglas Fir, and hemlock. Drop siding may be surfaced and matched, or shiplapped. Knotty grades of cedar (Select Tight Knot (STK)) and redwood (Rustic) are commonly available.

Flooring—Flooring is made chiefly from hardwoods, such as oak and maple, and the harder softwood species, such as Douglas-fir, western larch, and Southern Pine. Often, at least one softwood and one hardwood are stocked. Flooring is usually 19 mm (nominal 1 in.) thick. Thicker flooring is available for heavy-duty floors. Thinner flooring is

available, especially for re-covering old floors. Vertical- and flat-grained (also called quartersawn and plainsawn) flooring is manufactured from both softwoods and hardwoods. Vertical-grained flooring shrinks and swells less than flat-grained flooring, is more uniform in texture, and wears more uniformly, and the edge joints have less tendency to open.

Softwood flooring is usually available in B&BTR, C Select, or D Select grades. In maple, the chief grades are Clear, No. 1, and No. 2. The grades in quartersawn oak are Clear and Select, and in plainsawn, Clear, Select, and No. 1 Common. Quartersawn hardwood flooring has the same advantages as does vertical-grained softwood flooring. In addition, the silver or flaked grain of quartersawn flooring is frequently preferred to the figure of plainsawn flooring.

Casing and Base—Casing and base are standard items in the more important softwoods and are stocked in most yards in at least one species. The chief grade, B&BTR, is designed to meet the requirements of interior trim for dwellings. Many casing and base patterns are surfaced to 17 by 57 mm (11/16 by 2-1/4 in.); other sizes include 14 mm (9/16 in.) by 76 mm (3 in.), by 83 mm (3-1/4 in.), and by 89 mm (3-1/2 in.). Hardwoods for the same purposes, such as oak and birch, may be carried in stock in the retail yard or obtained on special order.

Shingles and Shakes—Commonly available shingles are sawn from western redcedar and northern white-cedar. For western redcedar, the shingle grades are No. 1, No. 2, and No. 3; for northern white-cedar, Extra, Clear, 2nd Clear, Clearwall, and Utility.

Shingles that contain only heartwood are more resistant to decay than are shingles that contain sapwood. Edge-grained shingles are less likely to warp and split than flat-grained shingles, thick-butted shingles less likely than thin-butted shingles, and narrow shingles less likely than wide shingles. The standard thickness values of thin-butted shingles are described as 4/2, 5/2-1/4, and 5/2 (four shingles to 51 mm (2 in.) of butt thickness, five shingles to 57 mm (2-1/4 in.) of butt thickness, and five shingles to 51 mm (2 in.) of butt thickness). Lengths may be 406, 457, or 610 mm (16, 18, or 24 in.). Random widths and specified (“dimension” shingle) widths are available in western redcedar, redwood, and cypress.

Shingles are usually packed four bundles to a square. A square of shingles will cover roughly 9 m² (100 ft²) of roof area when the shingles are applied at standard weather exposures.

Shakes are hand split or hand split and resawn from western redcedar. Shakes are of a single grade and must be 100% clear. In the case of hand split and resawn material, shakes are graded from the split face. Hand-split shakes are graded from the best face. Shakes must be 100% heartwood. The standard thickness of shakes ranges from 9.5 to 32 mm (3/8 to 1-1/4 in.). Lengths are 457 and 610 mm (18 and

24 in.), with a special “Starter–Finish Course” length of 381 mm (15 in.).

Pallet and Container Stock—Wood is often manufactured into lengths and sizes for wooden pallets and containers. As with other uses of wood, pallet and container stock must meet minimum wood quality requirements for checks, splits, shakes, wane, cross grain, decay, knots, and warp that are specific to their intended application. A detailed description of the recognized minimum quality requirements for wood used in the principal types of wood pallets is documented in Uniform Standard for Wood Pallets, and that for packaging is detailed in the Uniform Standard for Wood Containers produced by the National Wooden Pallet and Container Association (NWPCA 2007, 2009). See these documents for a more complete description of terms commonly understood among manufacturers, repairers, distributors, and users of wood pallets and containers. The specifications are specific to the expected number of uses, single or multiple, the item being manufactured is expected to see.

Important Purchase Considerations

Some points to consider when ordering lumber or timbers are the following:

1. **Quantity**—Lineal measure, board measure, surface measure, number of pieces of definite size and length. Consider that the board measure depends on the thickness and width nomenclature used and that the interpretation of these must be clearly delineated. In other words, such features as nominal or actual dimensions and pattern size must be considered.
2. **Size**—Thickness in millimeters or inches—nominal or actual if surfaced on faces; width in millimeters or inches—nominal or actual if surfaced on edges; length in meters or feet—may be nominal average length, limiting length, or a single uniform length. Often a trade designation, “random” length, is used to denote a nonspecified assortment of lengths. Such an assortment should contain critical lengths as well as a range. The limits allowed in making the assortment random can be established at the time of purchase.
3. **Grade**—As indicated in grading rules of lumber manufacturing associations. In softwoods that are in compliance with the American Softwood Lumber Standard, each piece of lumber may be grade stamped with its official grade designation, species identification, a name or number identifying the producing mill, the dryness at the time of surfacing, and a symbol identifying the inspection agency supervising the grading inspection. The grade designation stamped on a piece indicates the quality at the time the piece was graded. Subsequent exposure to unfavorable storage conditions, improper drying, or careless handling may cause the material to fall below its original grade.

Working or recutting a graded product to a pattern may change or invalidate the original grade. The purchase

Table 6–8. Standards and specifications for round timbers and ties^a

| Product | Material requirements | Preservative treatment | Engineering design stresses | |
|--------------------|-------------------------|--------------------------------------|-----------------------------|-------------------------|
| | | | Procedures | Design values |
| Utility poles | ANSI O5.1 | AWPA Commodity Specification D | — | ANSI O5.1 |
| Construction poles | ANSI O5.1 | AWPA Commodity Specification D | ASTM D 3200 | ASAE EP 388 |
| Piles | ASTM D 25 | AWPA Commodity Specification E | ASTM D 2899 | NDS |
| Construction logs | (See material supplier) | — | ASTM D 3957 | (See material supplier) |
| Ties | AREA | AWPA Commodity Specification C, AREA | — | AREA |

^aANSI, American National Standards Institute; ASTM, ASTM International; ASAE, American Society of Agricultural Engineers; AREA, American Railway Engineers Association; NDS, National Design Specification (for Wood Construction); AWPA, American Wood Protection Association.

specification should be clear in regard to regrading or acceptance of worked lumber. In softwood lumber, grades for dry lumber generally are determined after kiln drying and surfacing. However, this practice is not general for hardwood Factory lumber, where the grade is generally based on quality and size prior to kiln drying. To be certain the product grade is correct, refer to the grading rule by number and paragraph.

4. Species or species group of wood—Such as Douglas Fir, Southern Pine, Hem–Fir. Some species have been grouped for marketing convenience; others are sold under a variety of names. Be sure the species or species group is correctly and clearly described on the purchase specification.
5. Product—Such as flooring, siding, timbers, boards. Nomenclature varies by species, region, and grading association. To be certain the nomenclature is correct for the product, refer to the grading rule by number and paragraph.
6. Condition of seasoning—Such as air dry, kiln dry. Softwood lumber less than 114 mm (nominal 5 in.) in thickness dried to 19% moisture content or less is defined as dry by the American Softwood Lumber Standard. Kiln-dried lumber is lumber that has been seasoned in a chamber to a predetermined moisture content by applying heat. For lumber of nominal 5-in. or greater in thickness, some species are defined as dry having a maximum moisture content of greater than 19%. Green lumber is lumber less than 114 mm (nominal 5 in.) in thickness that has a moisture content in excess of 19%. For lumber of nominal 5-in. or greater thickness, green shall be defined in accordance with the provision of the applicable grading rules. If the moisture requirement is critical, the level of moisture content and the method by which it will be achieved must be specified.
7. Surfacing and working—Rough (unplaned), surfaced (dressed, planed), or patterned stock. Specify condition. If surfaced, indicate code (S4S, S1S1E). If patterned, list pattern number with reference to appropriate grade rules.
8. Grading rules—Official grading agency name and name of official rules under which product is graded, product identification, paragraph and page number of rules, and date of rules or official rule edition may be specified by the buyer.
9. Manufacturer—Name of manufacturer or trade name of specific product or both. Most lumber products are sold without reference to a specific manufacturer. If proprietary names or quality features of a manufacturer are required, this must be stipulated clearly on the purchase agreement.
10. Structural lumber and timbers should be stamped by an agency accredited by the Board of Review of the American Lumber Standard Committee.
11. Reinspection—Procedures for resolution of purchase disputes. The American Softwood Lumber Standard provides for procedures to be followed in resolution of manufacturer–wholesaler–consumer conflicts over quality or quantity of ALS lumber grades. The dispute may be resolved by reinspecting the shipment. Time limits, liability, costs, and complaint procedures are outlined in the grade rules of both softwood and hardwood agencies under which the disputed shipment was graded and purchased.

Round Timbers and Ties Standards and Specifications

Material standards and specifications listed in Table 6–8 were created through the joint efforts of producers and users to ensure compatibility between product quality and end use. These guidelines include recommendations for production, treatment, and engineering design. They are updated periodically to conform to changes in material and design technology.

Material Requirements

Round timber and tie material requirements vary with intended use. The majority of uses involve exposure to harsh



Figure 6–4.
An example
of round
timber poles
used for
electrical
utility
distribution.

environments. Thus, in addition to availability, form, and weight, durability is also an important consideration for the use of round timbers and ties. Availability reflects the economic feasibility of procuring members of the required size and grade. Form or physical appearance refers to visual characteristics, such as straightness and occurrence of knots and spiral grain. Weight affects shipping and handling costs and is a function of volume, moisture content, and wood density. Durability is directly related to expected service life and is a function of treatability and natural decay resistance. Finally, regardless of the application, any structural member must be strong enough to resist imposed loads with a reasonable factor of safety. Material specifications available for most applications of round timbers and ties contain guidelines for evaluating these factors.

Availability

Material evaluation begins with an assessment of availability. For some applications, local species of timber may be readily available in an acceptable form and quality. However, this is not normally the case. Pole producers and tie mills are scattered throughout heavily forested regions. Their products are shipped to users throughout North America.

Poles

Most structural applications of poles require timbers that are relatively straight and free of large knots. Poles used to support electric utility distribution and transmission lines (Fig. 6–4) range in length from 6 to 38 m (20 to 125 ft) and from 0.13 to 0.76 m (5 to 30 in.) in diameter, 1.8 m (6 ft) from the butt. Poles used to support local area distribution lines are normally <15 m (<50 ft) long and are predominately Southern Pine.

Hardwood species can be used for poles when the trees are of suitable size and form; their use is limited, however, by their weight, by their excessive checking, and because of the lack of experience in preservative treatment of hardwoods. Thus, most poles are softwoods.

The Southern Pine lumber group (principally loblolly, longleaf, shortleaf, and slash) accounts for roughly 80% of poles treated in the United States. Three traits of these pines account for their extensive use: thick and easily treated sapwood, favorable strength properties and form, and availability in popular pole sizes. In longer lengths, Southern Pine poles are in limited supply, so Douglas-fir, and to some extent western redcedar, ponderosa pine, and western larch, are used to meet requirements for 15-m (50-ft) and longer transmission poles.

Douglas-fir is used throughout the United States for transmission poles and is used in the Pacific Coast region for distribution and building poles. Because the heartwood of Douglas-fir is resistant to preservative penetration and has limited decay and termite resistance, serviceable poles need a well-treated shell of sapwood that is free of checking. To minimize checking after treatment, poles should be adequately seasoned or conditioned before treatment. With these precautions, the poles should compare favorably with treated Southern Pine poles in serviceability.

A small percentage of the poles treated in the United States are of western redcedar, produced mostly in British Columbia. The number of poles of this species used without treatment is not known but is considered to be small. Used primarily for utility lines in northern and western United States, well-treated redcedar poles have a service life that compares favorably with poles made from other species and could be used effectively in pole-type buildings.

Lodgepole pine is also used in small quantities for treated poles. This species is used both for utility lines and for pole-type buildings. It has a good service record when well treated. Special attention is necessary, however, to obtain poles with sufficient sapwood thickness to ensure adequate penetration of preservative, because the heartwood is not usually penetrated and is not decay resistant. The poles must also be well seasoned prior to treatment to avoid checking and exposure of unpenetrated heartwood to attack by decay fungi.

Western larch poles produced in Montana and Idaho came into use after World War II because of their favorable size, shape, and strength properties. Western larch requires preservative treatment full length for use in most areas and, as in the case of lodgepole pine poles, must be selected for adequate sapwood thickness and must be well seasoned prior to treatment. Other species occasionally used for poles are listed in the American National Standards Institute (ANSI) O5.1 standard. These minor species make up a very small portion of pole production and are used locally. Glued-laminated, or glulam, poles are also available for use where



Figure 6–5. Logs are used to construct logging bridges in remote forest areas.

special sizes or shapes are required. The ANSI Standard O5.2 provides guidelines for specifying these poles.

Piles

Material available for timber piles is more restricted than that for poles. Most timber piles used in the eastern half of the United States are Southern Pine, while those used in western United States are coast Douglas-fir. Oak, red pine, and cedar piles are also referenced in timber pile literature but are not as widely used as Southern Pine and Douglas-fir.

Construction Logs

Round timbers have been used in a variety of structures, including bridges, log cabins, and pole buildings. Log stringer bridges (Fig. 6–5) are generally designed for a limited life on logging roads intended to provide access to remote areas. In Alaska where logs may exceed 1 m (3 ft) in diameter, bridge spans may exceed 9 m (30 ft). Building poles, on the other hand, are preservative-treated logs in the 0.15- to 0.25-m- (6- to 10-in.-) diameter range. These poles rarely exceed 9 m (30 ft) in length. Although poles sold for this application are predominately Southern Pine, there is potential for competition from local species in this category. Finally, log cabin logs normally range from 0.2 to 0.25 m (8 to 10 in.) in diameter, and the availability of logs in this size range is not often a problem. However, because logs are not normally preservative-treated for this application, those species that offer moderate to high natural decay resistance, such as western redcedar, are preferred. Pole buildings, which incorporate round timbers as vertical columns and cantilever supports, require preservative-treated wood. Preservative-treated poles for this use may not be readily available.

Ties

The most important availability consideration for railroad cross ties is quantity. Ties are produced from most native species of timber that yield log lengths >2.4 m (8 ft) with diameters >0.18 m (7 in.). The American Railway Engineering Association (AREA) lists 26 U.S. species that may be

Table 6–9. Circumference taper

| Species | Change in circumference per meter (cm) | Change in circumference per foot ^a (in.) |
|-------------------------------|--|---|
| Western redcedar | 3.7 | 0.38 |
| Ponderosa pine | 2.4 | 0.29 |
| Jack, lodgepole, and red pine | 2.5 | 0.30 |
| Southern Pine | 2.1 | 0.25 |
| Douglas-fir, larch | 1.7 | 0.21 |
| Western hemlock | 1.7 | 0.20 |

^aTaken from ANSI O5.1.

used for ties. Thus, the tie market provides a use for many low-grade hardwood and softwood logs.

Form

Natural growth properties of trees play an important role in their use as structural round timbers. Three important form considerations are cross-sectional dimensions, straightness, and the presence of surface characteristics such as knots.

Poles and Piles

Standards for poles and piles have been written with the assumption that trees have a round cross section with a circumference that decreases linearly with height. Thus, the shape of a pole or pile is often assumed to be that of the frustum of a cone. Actual measurements of tree shape indicate that taper is rarely linear and often varies with location along the height of the tree. Average taper values from the ANSI O5.1 standard are shown in Table 6–9 for the more popular pole species. Guidelines to account for the effect of taper on the location of the critical section above the groundline are given in ANSI O5.1. The standard also tabulates pole dimensions for up to 15 size classes of 11 major pole species.

Taper also affects construction detailing of pole buildings. Where siding or other exterior covering is applied, poles are generally set with the taper to the interior side of the structures to provide a vertical exterior surface (Fig. 6–6).

Another common practice is to modify the round poles by slabbing to provide a continuous flat face. The slabbed face permits more secure attachment of sheathing and framing members and facilitates the alignment and setting of intermediate wall and corner poles. The slabbing consists of a minimum cut to provide a single continuous flat face from the groundline to the top of intermediate wall poles and two continuous flat faces at right angles to one another from the groundline to the top of corner poles. However, preservative penetration is generally limited to the sapwood of most species; therefore slabbing, particularly in the groundline area of poles with thin sapwood, may result in somewhat less protection than that of an unslabbed pole. All cutting and sawing should be confined to that portion of the pole above the groundline and should be performed before treatment.

The ASTM International (formerly American Society for Testing and Materials) standard ASTM D 25 provides tables of pile sizes for either friction piles or end-bearing piles. Friction piles rely on skin friction rather than tip area for support, whereas end-bearing piles resist compressive force at the tip. For this reason, a friction pile is specified by butt circumference and may have a smaller tip than an end-bearing pile. Conversely, end-bearing piles are specified by tip area and butt circumference is minimized.

Straightness of poles or piles is determined by two form properties: sweep and crook. Sweep is a measure of bow or gradual deviation from a straight line joining the ends of the pole or pile. Crook is an abrupt change in direction of the centroidal axis. Limits on these two properties are specified in both ANSI O5.1 and ASTM D 25.

Construction Logs

Logs used in construction are generally specified to meet the same criteria for straightness and knots as poles and piles (ASTM D 25). For log stringer bridges, the log selection criteria may vary with the experience of the person doing the selection, but straightness, spiral grain, wind shake, and knots are limiting criteria. Although no consensus standard is available for specifying and designing log stringers, the *Design Guide for Native Log Stringer Bridges* was prepared by the U.S. Forest Service.

Logs used for log cabins come in a wide variety of cross-sectional shapes (Fig. 6–7). Commercial cabin logs are usually milled so that their shape is uniform along their length. The ASTM D 3957 standard, a guide for establishing stress grades for building logs, recommends stress grading on the basis of the largest rectangular section that can be inscribed totally within the log section. The standard also provides commentary on the effects of knots and slope of grain.

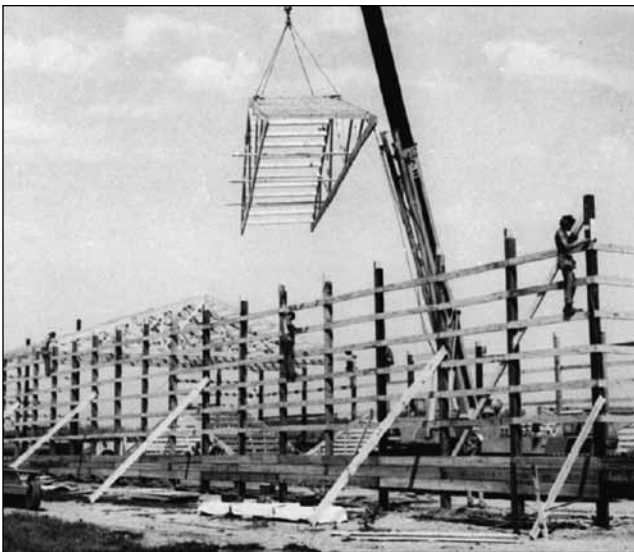


Figure 6–6. Poles provide economical foundation and wall systems for agricultural and storage buildings.

Ties

Railroad ties are commonly shaped to a fairly uniform section along their length. The American Railway Engineering Association (AREA) publishes specifications for the sizes, which include seven size classes ranging from 0.13 by 0.13 m (5 by 5 in.) to 0.18 by 0.25 m (7 by 10 in.). These tie classes may be ordered in any of three standard lengths: 2.4 m (8 ft), 2.6 m (8.5 ft), or 2.7 m (9 ft).

Weight and Volume

The weight of any wood product is a function of its volume, density, moisture content, and any retained treatment substance. An accurate estimate of volume of a round pole would require numerous measurements of the circumference and shape along the length, because poles commonly exhibit neither a uniform linear taper nor a perfectly round shape. The American Wood Protection Association (AWPA) Factor 3 section therefore recommends volume estimates be based on the assumption that the pole is shaped as the frustum of a cone (that is, a cone with the top cut perpendicular to the axis), with adjustments dependent on species. The volume in this case is determined as the average cross-sectional area A times the length. Estimates of average cross-sectional area may be obtained either by measuring the circumference at mid-length ($A = C_m^2/4\pi$) or taking the average of the butt and tip diameters ($A = \pi(D + d)^2/16$) to estimate the area of a circle. The AWPA recommends that these estimates then be adjusted by the following correction factors for the given species and application:

| | |
|----------------------------------|------|
| Oak piles | 0.82 |
| Southern Pine piles | 0.93 |
| Southern Pine and red pine poles | 0.95 |

Tables for round timber volume are given in AWPA Factor 3 tables. The volume of a round timber differs little whether it is green or dry. Drying of round timbers causes checks to open, but there is little reduction of the gross diameter of the pole.

Wood density also differs with species, age, and growing conditions. It will even vary along the height of a single tree. Average values, tabulated by species, are normally expressed as specific gravity (SG), which is density expressed as a ratio of the density of water (see Chap. 5). For commercial species grown in the United States, SG varies from

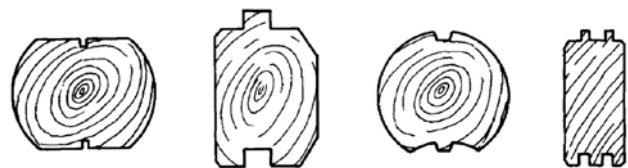


Figure 6–7. Construction logs can be formed in a variety of shapes for log homes. Vertical surfaces may be varied for aesthetic purposes, while the horizontal surfaces generally reflect structural and thermal considerations.

0.32 to 0.65. If you know the green volume of a round timber and its SG, its dry weight is a product of its SG, its volume, and the unit weight of water (1,000 kg m⁻³ (62.4 lb ft⁻³)). Wood moisture content can also be highly variable. A pole cut in the spring when sap is flowing may have a moisture content exceeding 100% (the weight of the water it contains may exceed the weight of the dry wood substance). If you know the moisture content (MC) of the timber, multiply the dry weight by (1 + MC/100) to get the wet weight.

Finally, in estimating the weight of a treated wood product such as a pole, pile, or tie, you must take into account the weight of the preservative. Recommended preservative retentions are listed in Table 15–1 in Chapter 15. By knowing the volume, the preservative weight can be approximated by multiplying volume by the recommended preservative retention. This estimation will err on the side of overestimating preservative weight because the actual retention specifications are based on an outer assay zone and not the entire volume.

Durability

For most applications of round timbers and ties, durability is primarily a question of decay resistance. Some species are noted for their natural decay resistance; however, even these may require preservative treatment, depending upon the environmental conditions under which the material is used and the required service life. For some applications, natural decay resistance is sufficient. This is the case for temporary piles, marine piles in fresh water entirely below the permanent water level, and construction logs used in building construction. Any wood members used in ground contact should be pressure treated, and the first two or three logs above a concrete foundation should be brush treated with a preservative–sealer.

Preservative Treatment

The American Wood Protection Association (AWPA) standards covers the inspection and treatment requirements for various wood products including poles, piles, and ties. Federal Specification TT–W–571 (U.S. Federal Supply Service (USFSS)) is no longer current, and government specifiers now use AWPA standards.) AWPA Standard T1 contains general pressure treatment specifications, Commodity Specification A covers treatment of lumber timbers, Commodity Specification C covers treatment of ties, Commodity Specification D covers pressure and thermal treatment of poles, and Commodity Specification E covers round timber piles. The AREA specifications for cross ties and switch ties also cover preservative treatment. Retention and types of various preservatives recommended for various applications are given in Table 15–1.

Inspection and treatment of poles in service has been effective in prolonging the useful life of untreated poles and those with inadequate preservative penetration or retention.

The Forest Research Laboratory at Oregon State University has published guidelines for developing an in-service pole maintenance program.

Service Life

Service conditions for round timbers and ties vary from mild for construction logs to severe for cross ties. Construction logs used in log homes may last indefinitely if kept dry and properly protected from insects. Most railroad ties, on the other hand, are continually in ground contact and are subject to mechanical damage.

Poles

The life of poles can vary within wide limits, depending upon properties of the pole, preservative treatments, service conditions, and maintenance practices. In distribution or transmission line supports, however, service life is often limited by obsolescence of the line rather than the physical life of the pole.

It is common to report the average life of untreated or treated poles based on observations over a period of years. These average life values are useful as a rough guide to the service life to be expected from a group of poles, but it should be kept in mind that, within a given group, 60% of the poles will have failed before reaching an age equal to the average life.

Early or premature failure of treated poles can generally be attributed to one or more of three factors: (a) poor penetration and distribution of preservative, (b) an inadequate retention of preservative, or (c) use of a substandard preservative. Properly treated poles can last 50 years or longer.

Western redcedar is one species with a naturally decay-resistant heartwood. If used without treatment, however, the average life is somewhat less than 20 years.

Piles

The expected life of a pile is also determined by treatment and use. Wood that remains completely submerged in water does not decay, although bacteria may cause some degradation; therefore, decay resistance is not necessary in all piles, but it is necessary in any part of the pile that may extend above the permanent water level. When piles that support the foundations of bridges or buildings are to be cut off above the permanent water level, they should be pressure treated to conform to recognized specifications such as AWPA Commodity Specification E. The untreated surfaces exposed at the cutoffs should also be given protection by thoroughly brushing the cut surface with copper naphthenate containing at least 1% elemental copper. A coat of pitch, asphalt, or similar material may then be applied over the creosote and a protective sheet material, such as metal, roofing felt, or saturated fabric, should be fitted over the pile cut-off in accordance with AWPA Standard M4. Correct application and maintenance of these materials are critical in maintaining the integrity of piles.

Chapter 6 Commercial Lumber, Round Timbers, and Ties

Piles driven into earth that is not constantly wet are subject to about the same service conditions as apply to poles but are generally required to last longer. Preservative retention requirements for piles are therefore sometimes greater than for poles (Table 15–1). Piles used in salt water are subject to destruction by marine borers even though they do not decay below the waterline. The most effective practical protection against marine borers has been a treatment first with a waterborne preservative, followed by seasoning with a creosote treatment. Other preservative treatments of marine piles are covered in AWWA Commodity Specification E and shown in Table 15–2.

Ties

The life of ties in service depends on their ability to resist decay and mechanical destruction. Under sufficiently light traffic, heartwood ties of naturally durable wood, even if of low strength, may give 10 or 15 years of average service without preservative treatment; under heavy traffic without adequate mechanical protection, the same ties might fail in 2 or 3 years. Advances in preservatives and treatment processes, coupled with increasing loads, are shifting the primary cause of tie failure from decay to mechanical damage. Well-treated ties, properly designed to carry intended loads, should last from 25 to 40 years on average. Records on life of treated and untreated ties are occasionally published in the annual proceedings of the AREA and AWWA.

Commonly Used Lumber, Round Timber, and Tie Abbreviations

The following standard lumber abbreviations are commonly used in contracts and other documents for purchase and sale of lumber.

| | |
|------------|---|
| AAR | Association of American Railroads |
| AD | air dried |
| ADF | after deducting freight |
| AF | alpine fir |
| ALS | American Lumber Standard |
| AST | antistain treated; at ship tackle (western softwoods) |
| AV or avg | Average |
| AW&L | all widths and lengths |
| B1S | see EB1S, CB1S, and E&CB1S |
| B2S | see EB2S, CB2S, and E&CB2S |
| B&B, B&BTR | B and Better |
| B&S | beams and stringers |
| BD | Board |
| BD FT | board feet |
| BDL | Bundle |
| BEV | bevel or beveled |
| BH | boxed heart |
| B/L, BL | bill of lading |
| BM | board measure |
| BSND | bright sapwood, no defect |

| | |
|------------------------------|--|
| BTR | Better |
| CB | center beaded |
| CB1S | center bead on one side |
| CB2S | center bead on two sides |
| CC | cubical content |
| cft or cu. ft. | cubic foot or feet |
| CF | cost and freight |
| CIF | cost, insurance, and freight |
| CIFE | cost, insurance, freight, and exchange |
| CG2E | center groove on two edges |
| C/L | carload |
| CLG | ceiling |
| CLR | clear |
| CM | center matched |
| Com | Common |
| CONST | construction |
| CS | caulking seam |
| CSG | casing |
| CV | center V |
| CV1S | center V on one side |
| CV2S | center V on two sides |
| DB Clg | double-beaded ceiling (E&CB1S) |
| DB Part | double-beaded partition (E&CB2S) |
| DET | double end-trimmed |
| DF | Douglas-fir |
| DF–L | Douglas-fir plus larch |
| DIM | dimension |
| DKG | decking |
| D/S, DS, D/Sdg | drop siding |
| D1S, D2S | see S1S and S2S |
| D&M | dressed and matched |
| D&CM | dressed and center matched |
| D&SM | dressed and standard matched |
| D2S&CM | dressed two sides and center matched |
| D2S&SM | dressed two sides and standard matched |
| E | edge |
| EB1S | edge bead one side |
| EB2S, SB2S | edge bead on two sides |
| EE | eased edges |
| EG | edge (vertical or rift) grain |
| EM | end matched |
| EV1S, SV1S | edge V one side |
| EV2S, SV2S | edge V two sides |
| E&CB1S | edge and center bead one side |
| E&CB2S, DB2S, BC&2S | edge and center bead two sides |
| E&CV1S, DV1S, V&CV1S | edge and center V one side |
| E&CV2S, DV2S, V&CV2S | edge and center V two sides |
| ES | Engelmann spruce |
| $F_b, F_t, F_c, F_v, F_{cx}$ | allowable stress (MPa (lb/in ²)) in bending; tension, compression and shear parallel to grain; and in compression perpendicular to grain, respectively |
| FA | facial area |

| | | | |
|----------------|---|----------------|---|
| Fac | factory | NBM | net board measure |
| FAS | free alongside (vessel) | NOFMA | National Oak Flooring Manufacturers Association |
| FAS | Firsts and Seconds | No. | number |
| FAS1F | Firsts and Seconds one face | N1E or N2E | nosed one or two edges |
| FBM, Ft. BM | feet board measure | Ord | Order |
| FG | flat or slash grain | PAD | partially air-dried |
| FJ | finger joint; end-jointed lumber using finger-joint configuration | PAR, Par | paragraph |
| FLG, Flg | flooring | PART, Part | partition |
| FOB | free on board (named point) | PAT, Pat | pattern |
| FOHC | free of heart center | Pcs. | pieces |
| FOK | free of knots | PE | plain end |
| FRT, Frt | freight | PET | precision end-trimmed |
| FT, ft | foot, feet | PP | ponderosa pine |
| FT. SM | feet surface measure | P&T | posts and timbers |
| G | girth | P1S, P2S | see S1S and S2S |
| GM | grade marked | RDM | random |
| G/R | grooved roofing | REG, Reg | regular |
| HB, H.B. | hollow back | Rfg. | roofing |
| HEM | hemlock | RGH, Rgh | rough |
| H-F | mixed hemlock and fir (Hem–Fir) | R/L, RL | random lengths |
| Hrt | heart | R/W, RW | random widths |
| H&M | hit and miss | RES | resawn |
| H or M | hit or miss | SB1S | single bead one side |
| IC | incense cedar | SDG, Sdg | siding |
| IN, in. | inch, inches | S-DRY | surfaced dry; lumber ≤19% moisture content per ALS for softwood |
| Ind | industrial | SE | square edge |
| IWP | Idaho white pine | SEL, Sel | Select or Select grade |
| J&P | joists and planks | SE&S | square edge and sound |
| JTD | jointed | SG | slash or flat grain |
| KD | kiln dried | S-GRN | surfaced green; lumber unseasoned, >19% moisture content per ALS for softwood |
| KDAT | kiln-dried after treatment | SGSSND | sapwood, gum spots and streaks, no defect |
| L | western larch | SIT. SPR | Sitka spruce |
| LBR, Lbr | lumber | S/L, SL, S/Lap | shiplap |
| LCL | less than carload | SM | surface measure |
| LGR | longer | Specs | specifications |
| LGTH | length | SP | sugar pine |
| Lft, Lf | lineal foot, feet | SQ | square |
| LIN, Lin | lineal | SQRS | squares |
| LL | longleaf | SRB | stress-rated board |
| LNG, Lng | lining | STD, Std | standard |
| LP | lodgepole pine | Std. lgths. | standard lengths |
| M | thousand | STD. M | standard matched |
| MBM, MBF, M.BM | thousand (feet) board measure | SS | Sitka spruce |
| MC, M.C. | moisture content | SSE | sound square edge |
| MERCH, Merch | merchantable | SSND | sap stain, no defect (stained) |
| MFMA | Maple Flooring Manufacturers Association | STK | Select tight knot |
| MG | medium grain or mixed grain | STK | stock |
| MH | mountain hemlock | STPG | stepping |
| MLDG, Mldg | moulding | STR, STRUCT | structural |
| Mft | thousand feet | SYP | Southern Pine |
| M-S | mixed species | S&E | side and edge (surfaced on) |
| MSR | machine stress rated | S1E | surfaced one edge |
| N | nosed | S2E | surfaced two edges |

Chapter 6 Commercial Lumber, Round Timbers, and Ties

| | |
|----------|--|
| S1S | surfaced one side |
| S2S | surfaced two sides |
| S4S | surfaced four sides |
| S1S&CM | surfaced one side and center matched |
| S2S&CM | surfaced two sides and center matched |
| S4S&CS | surfaced four sides and caulking seam |
| S1S1E | surfaced one side, one edge |
| S1S2E | surfaced one side, two edges |
| S2S1E | surfaced two sides, one edge |
| S2S&SL | surfaced two sides and shiplapped |
| S2S&SM | surfaced two sides and standard matched |
| TBR | timber |
| T&G | tongued and grooved |
| TSO | treating service only (nonconforming to standard) |
| UTIL | utility |
| VG | vertical (edge) grain |
| V1S | see EV1S, CV1S, and E&CV1S |
| V2S | see EV2S, CV2S, and E&CV2S |
| WC | western cedar |
| WCH | West Coast hemlock |
| WCW | West Coast woods |
| WDR, wdr | wider |
| WF | white fir |
| WHAD | worm holes (defect) |
| WHND | worm holes (no defect) |
| WT | weight |
| WTH | width |
| WRC | western redcedar |
| WW | white woods (Engelmann spruce, any true firs, any hemlocks, any pines) |

NWPCA 2007. Uniform Standard for Wood Pallets. Alexandria, VA: National Wooden Pallet and Container Association. 49 p.

NWPCA 2009. Uniform Standard for Wood Containers. Alexandria, VA: National Wooden Pallet and Container Association. 44 p.

Smith, L. W.; Wood, L. W. 1964. History of yard lumber size standards. Madison, WI: U.S. Department of Agriculture, Forest Service, Forest Products Laboratory. 59 p.

References

ANSI. [Current edition]. ANSI O5.1. Specifications and dimensions for wood poles. New York, NY: American National Standards Institute.

ASTM. [Current edition]. ASTM D 3957. Standard methods for establishing stress grades for structural members used in log buildings. West Conshohocken, PA: ASTM International.

AWPA. [Current edition]. Book of standards (includes standards on pressure and thermal treatment of poles, piles, and ties). American Wood-Preserver's Bureau official quality control standards. Bethesda, MD: American Wood Protection Association.

DOC. [Current edition]. American softwood lumber standard. Voluntary Product Standard PS-20-94. Washington, DC: U.S. Department of Commerce.

Muchmore, F.W. 1977. Design guide for native log stringer bridges. Juneau, AK: U.S. Department of Agriculture, Forest Service, Region 10.

